


CMP SEMINAR@NTHU
OCT 3, 2006

CARRIER-MEDIATED
FERROMAGNETISM
AND
ITS POTENTIAL APPLICATIONS



HSIU-HAU LIN

NAT'L TSING-HUA UNIVERSITY
NAT'L CENTER FOR THEORETICAL SCIENCES

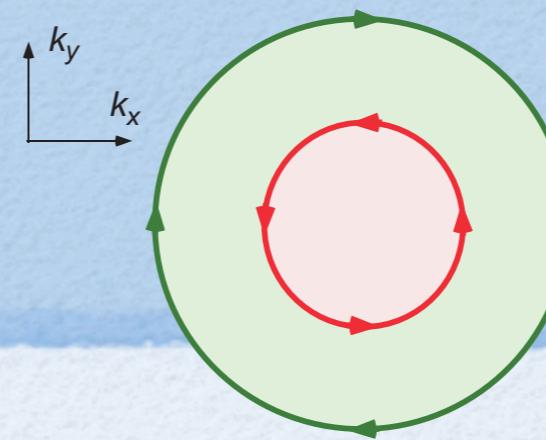

OUTLINE

- Diluted Magnetic Semiconductors
- Two-component Ferromagnetism
- Building Spin-Wave Theory
- Spin-Wave Relaxation
- Sprial Exchange
- Summary

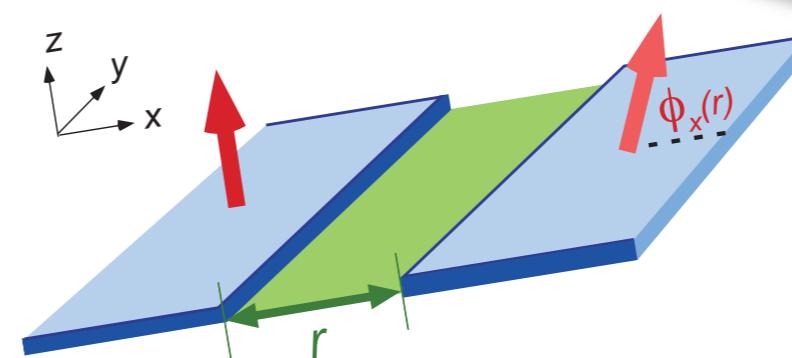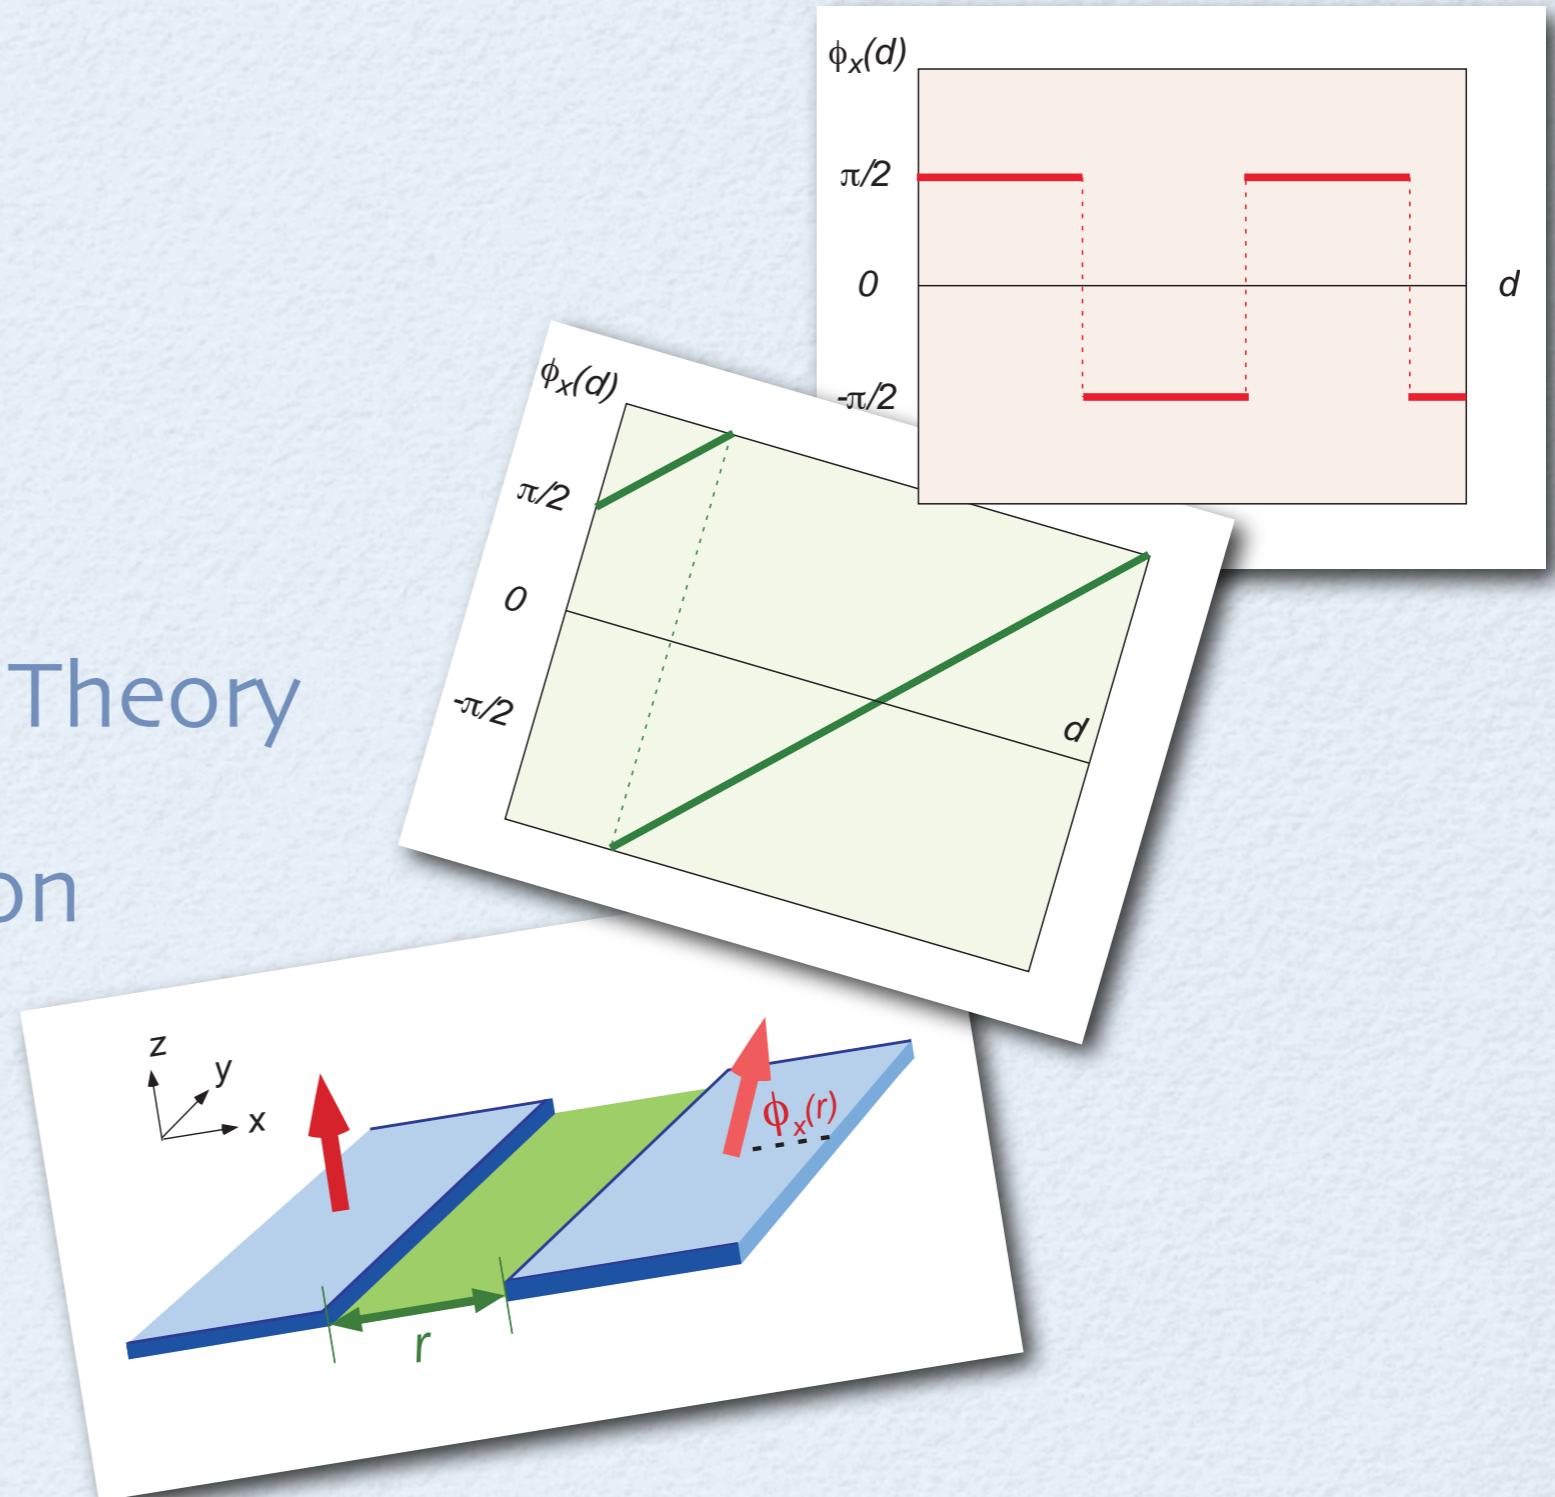

THAT'S HOW IT STARTED...

M.-F. Yang, S.-J. Sun & M.-C. Chang
Phys. Rev. Lett. 86, 5636 (2001)

J. Konig, HHL & A. H. MacDonald
Phys. Rev. Lett. 86, 5637 (2001)

Spiral exchange interaction in diluted magnetic semiconductor junction
S.-J. Sun, S.-S. Chen & HHL
Appl. Phys. Lett. 84, 2862 (2004)

Spin-wave relaxation in diluted magnetic semiconductors within the self-consistent Green's function approach
J. E. Bunder, S.-J. Sun & HHL
Appl. Phys. Lett. 89, 072101 (2006)

Noncollinear exchange coupling in a trilayer magnetic junction and its connection to Fermi surface topology

W.-M. Huang, C.-H. Chang & HHL
Phys. Rev. B 73, 241307(R) (2006)

Spiral exchange coupling in trilayer magnetic junction mediated by diluted-magnetic-semiconductor thin film


C.-H. Lin, HHL & T.-M. Hong
Appl. Phys. Lett. 89, 032503 (2006)

COLLABORATORS




DILUTED MAGNETIC SEMICONDUCTORS


Ferromagnetic (Ga,Mn) As

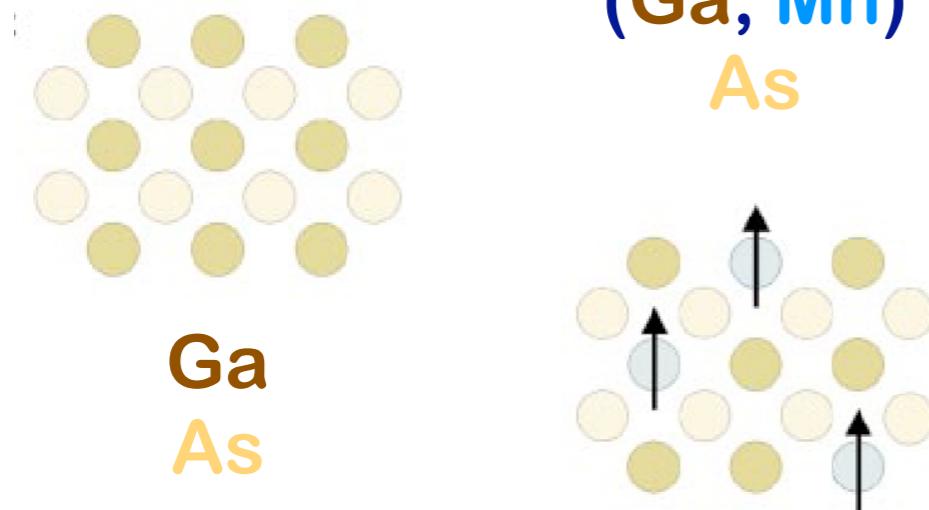

(Ga,Mn)As becomes
ferromagnetic below Curie
temperature T_c .


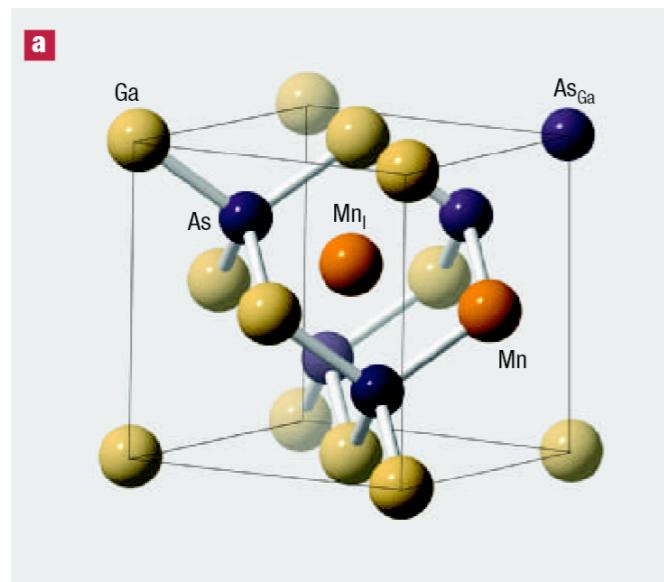


Zincblende structure of GaAs

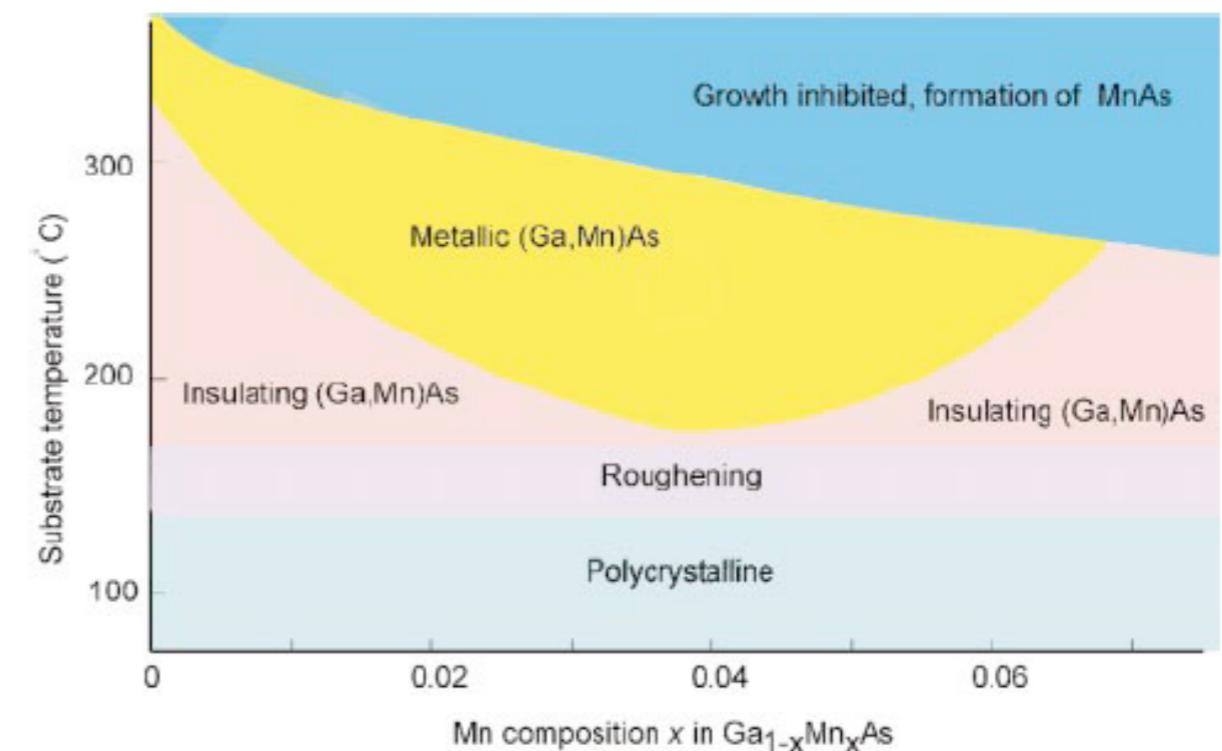

Curie Temperature

Magnetization is measured through **anomalous Hall effect**.

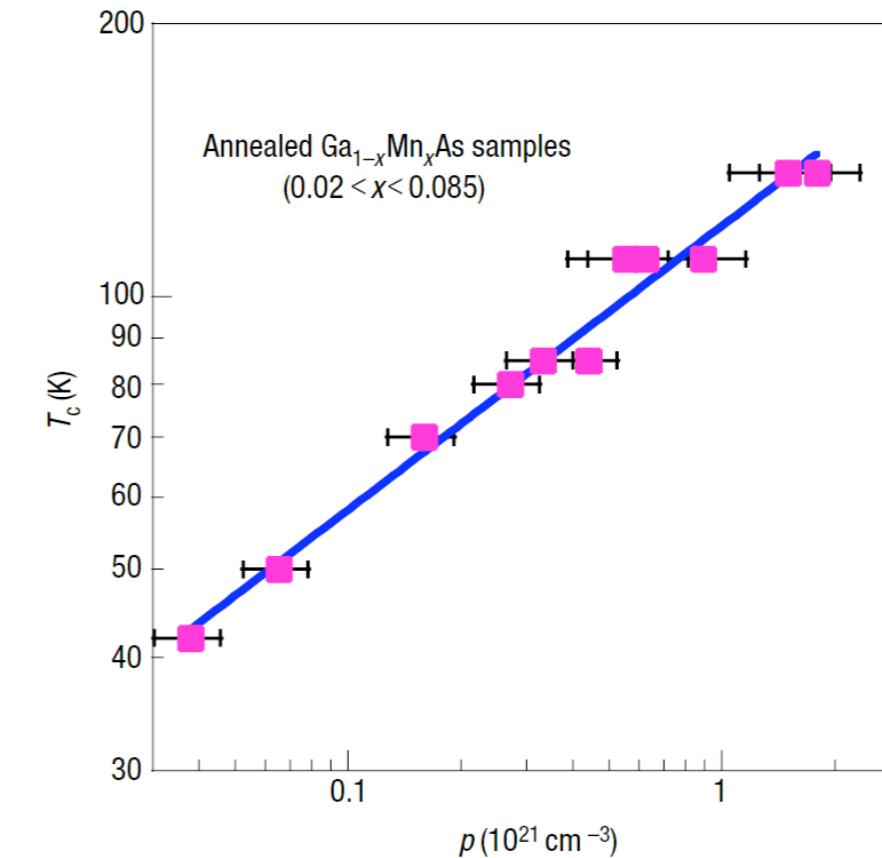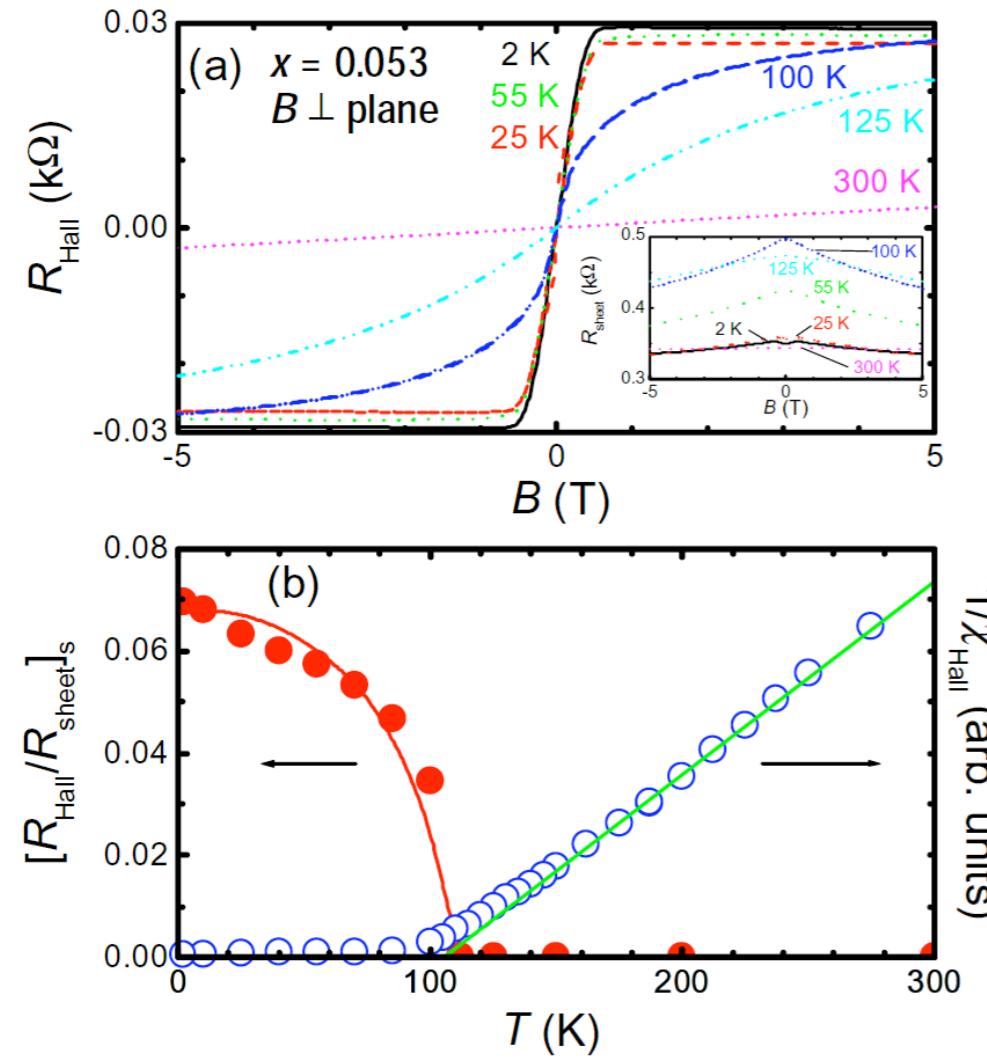


The trend of **Curie temperature** can be fitted rather well by the empirical power law versus the carrier density,

$$T_c \sim n_h^{1/3}$$

Transport and Field Effect


Ohno's Group
Nature 408, 944 (2000)

He, Yang, Ge, Wang, Dai, Wang
Appl. Phys. Lett. 87, 162506 (2005)

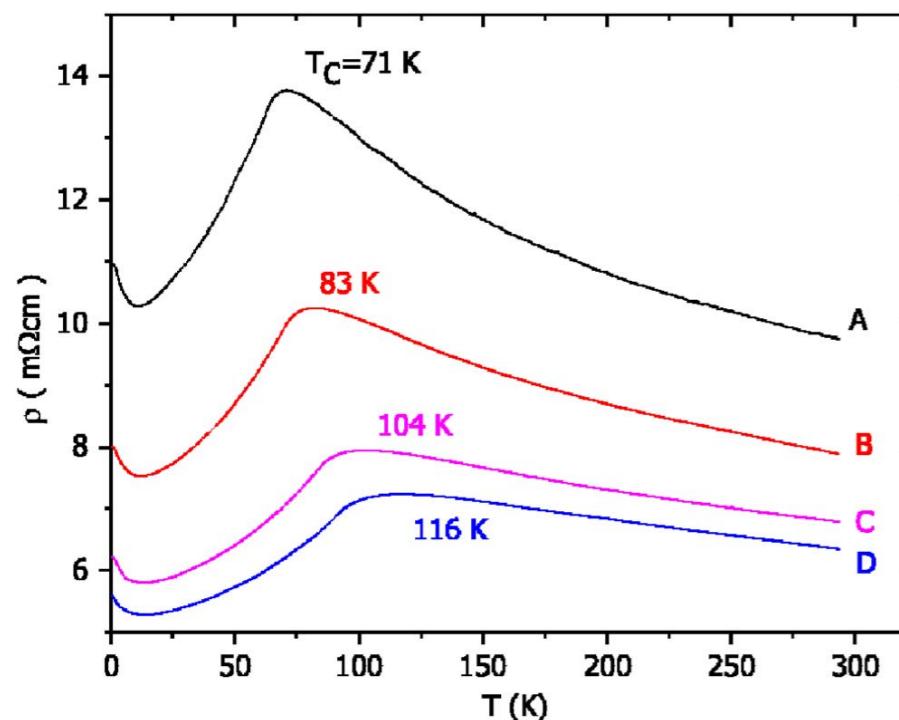


Resistivity shows pronounced peak around the Curie temperature. Is it the Fisher-Langer anomaly?

By varying the gate voltage, one can manipulate the concentration of itinerant carriers.

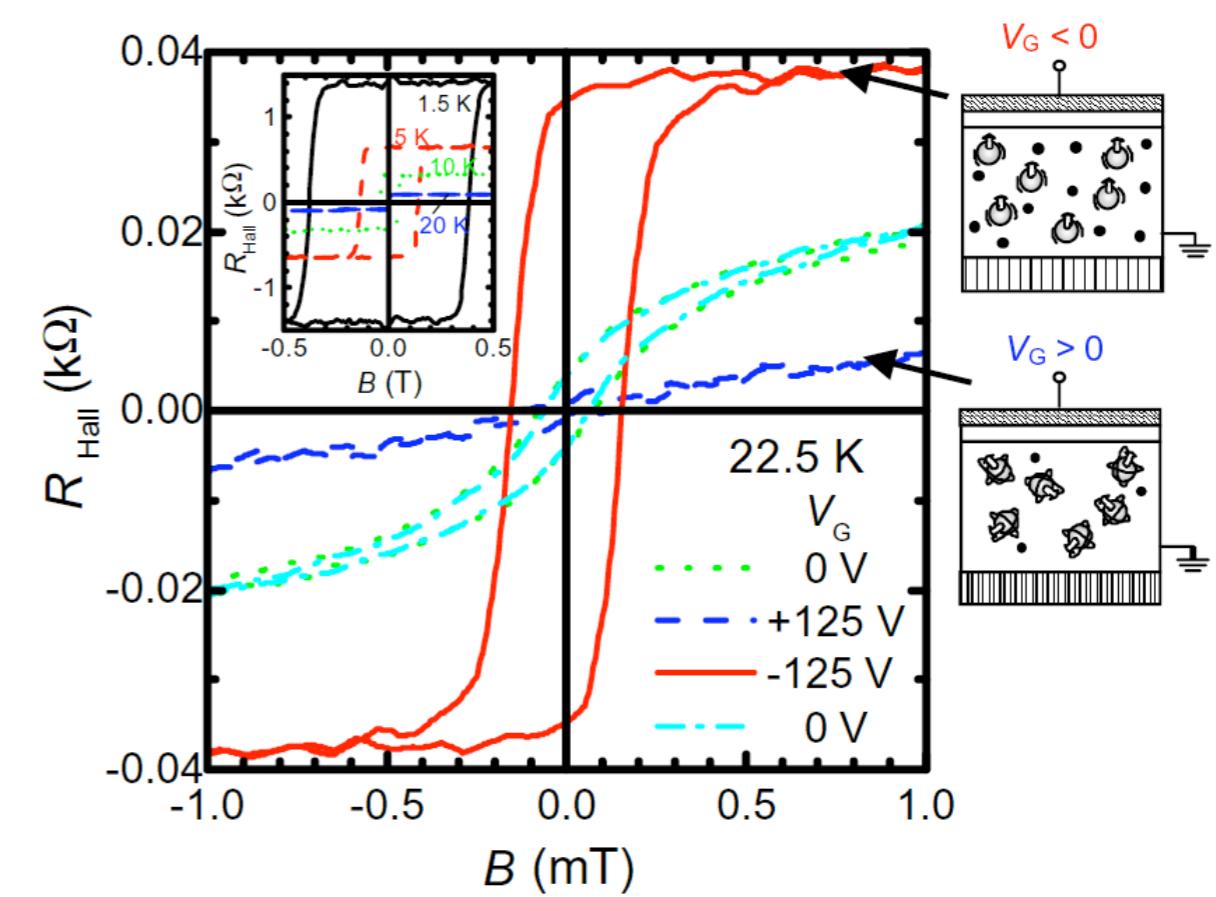


Spin Injection

Ohno's Group,
Nature 402, 790 (1999)

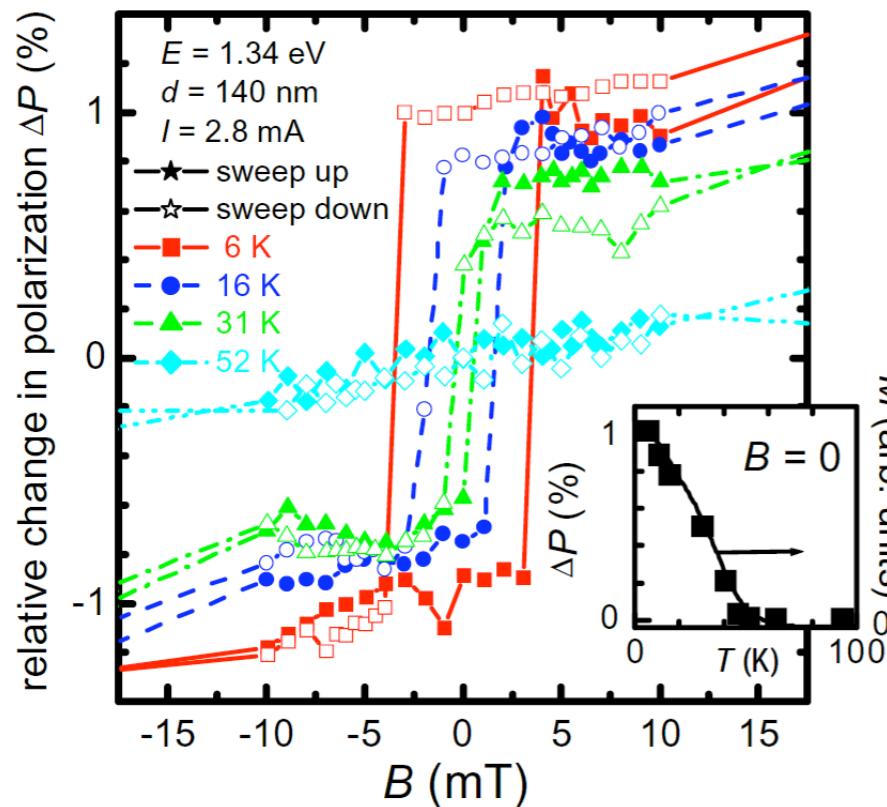

Polarized holes recombined with electrons, creating circularly polarized light by angular momentum transfer.

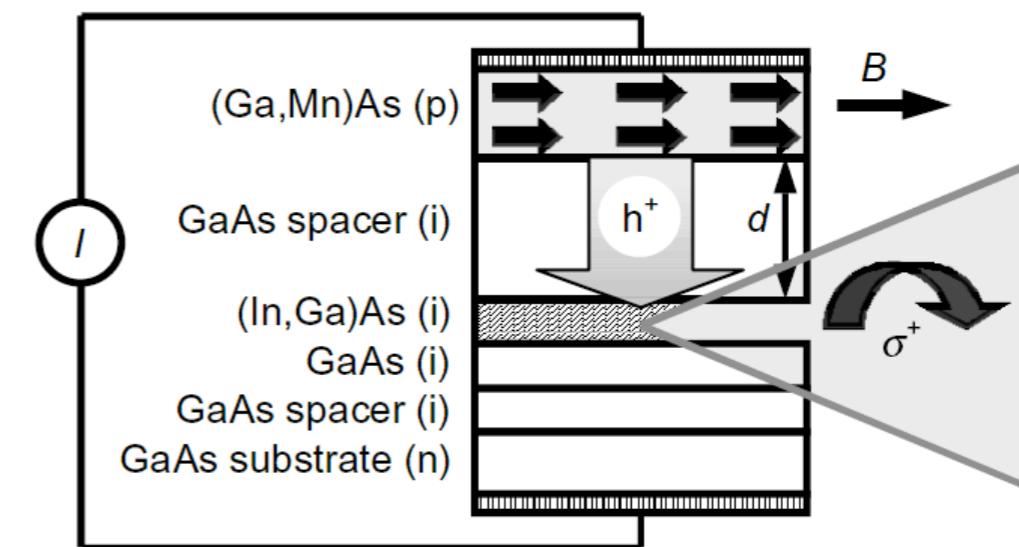


By measuring the intensity of the polarized light emission, we can estimate the efficiency of spin injection in the all-semiconductor setup.

TWO-COMPONENT FERROMAGNETISM



Carrier-Mediated Ferromagnetism

MacDonald et al.
Nature Materials 4, 195 (2005)

(a) At finite temperature, impurity spins prefer random orientations to maximize thermal entropy.

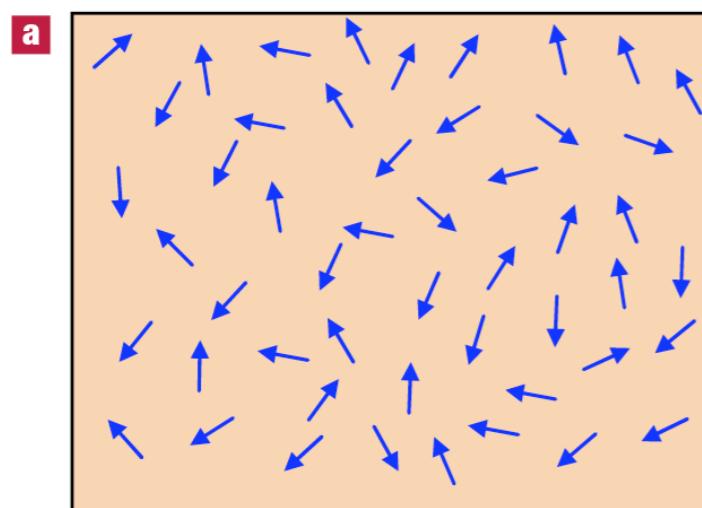

(b) The itinerant carriers like to align the impurity spins so that the kinetic energy is lowered.

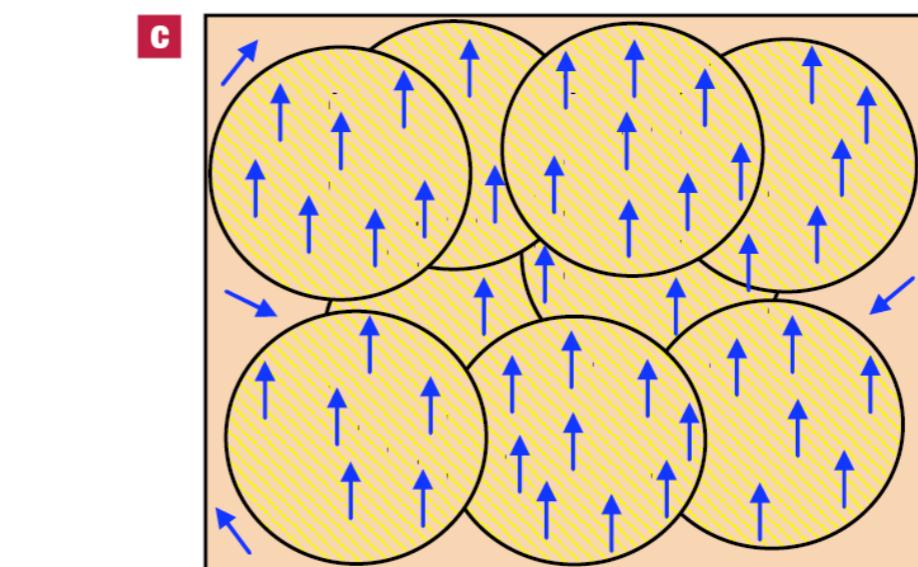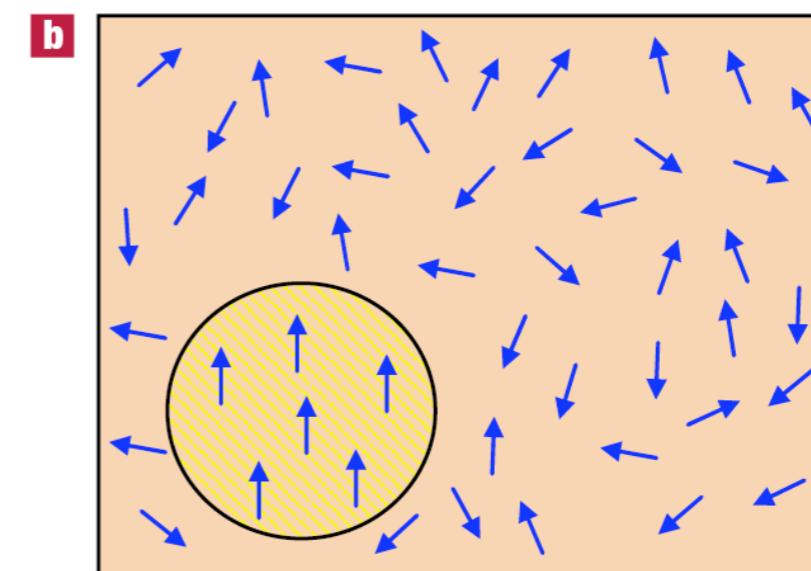

(c) Delocalization of itinerant carriers leads to ferromagnetism.

Model

We start with the simplest model containing both itinerant and localized spins,

$$H = \int d^3r \left\{ \psi^\dagger(r) \left(-\frac{\nabla^2}{2m^*} - \mu \right) \psi(r) + J \mathbf{S}(r) \cdot \boldsymbol{\sigma}(r) \right\},$$

where J is the exchange coupling between impurity and itinerant spin densities, denoted by $\mathbf{S}(r), \boldsymbol{\sigma}(r)$ respectively,

$$\begin{aligned} \mathbf{S}(r) &= \sum_I \delta^3(r - R_I) \mathbf{S}_I, \\ \boldsymbol{\sigma}(r) &= \frac{1}{2} \psi_\alpha^\dagger(r) \boldsymbol{\tau}_{\alpha\beta} \psi_\beta(r). \end{aligned}$$

Of course, the realistic diluted magnetic semiconductors are beyond the simple Hamiltonian, which ignores several important pieces of physics: (1) realistic electronic band structure, (2) electron-electron interactions, (3) direct exchange between impurity spins.

Mean-Field Decomposition

Split the spin operators into mean-field and fluctuating parts,

$$S = \langle S^z \rangle + \delta S, \quad \sigma = \langle \sigma^z \rangle + \delta \sigma,$$

and dropping higher-order fluctuations $\delta S \cdot \delta \sigma$, the exchange coupling is approximated by

$$\begin{aligned} S \cdot \sigma &\approx \langle S^z \rangle \langle \sigma^z \rangle + \langle S^z \rangle \delta \sigma + \langle \sigma^z \rangle \delta S \\ &= -\langle S^z \rangle \langle \sigma^z \rangle + \langle S^z \rangle \sigma^z + \langle \sigma^z \rangle S^z, \end{aligned}$$

Dropping the constant in the first term, the mean-field Hamiltonian $H_{MF} = H_h + H_I$ is

$$\begin{aligned} H_h &= \int d^3r \psi_\sigma^\dagger (\epsilon_\sigma - \mu) \psi_\sigma, \\ H_I &= \int d^3r J \langle \sigma^z \rangle S^z, \end{aligned}$$

where the spectrums for the itinerant carriers are split by the exchange coupling, $\epsilon_\sigma = p^2/2m^* + (\sigma/2)J\langle S^z \rangle$.

Self-Consistency (I)

For notational convenience, introduce the polarization for both components of spins,

$$\alpha_I = \frac{1}{n_I S} \langle S^z \rangle, \quad \alpha_h = -\frac{2}{n_h} \langle \sigma^z \rangle.$$

It is clear that the polarizations are always between zero and one, $0 \leq \alpha_I, \alpha_h \leq 1$. The minus sign is introduced in the second equation because the exchange coupling is antiferromagnetic.

With given polarization of the impurity spin α_I , one can proceed to compute the polarization of the itinerant carriers α_h . Note that the densities of itinerant carriers are

$$n_\nu = \int \frac{d^3 k}{(2\pi)^3} \frac{1}{e^{\beta(\epsilon_\nu - \mu)} + 1},$$

and the chemical potential μ is determined by keeping the total density of the itinerant carriers $n_\uparrow + n_\downarrow = n_h$ constant.

Self-Consistency (II)

Once the chemical potential is solved, the polarization of the itinerant carriers is

$$\alpha_h(\alpha_I, T) = \frac{n_\downarrow(\alpha_I, T) - n_\uparrow(\alpha_I, T)}{n_h}.$$


In general, $\alpha_h(\alpha_I, T)$ do not have a simple analytical form in terms of the impurity spin polarization α_I and the temperature T . To complete the self-consistency, we now compute the polarization of the impurity α_I with a given polarization α_h . The calculation leads to the Brillouin function,

$$\alpha_I(\alpha_h, T) = B_S \left[\left(\frac{Jn_h S}{2kT} \right) \alpha_h \right],$$

where the Brillouin function is $B_S(x) \equiv \frac{2S+1}{2S} \coth \left(\frac{2S+1}{2S} x \right) - \frac{1}{2S} \coth \left(\frac{1}{2S} x \right)$. The above equations complete the self-consistency loop in Weiss mean-field theory.

Mean-Field Prediction

The polarization can be evaluated in mean-field limit by replacing all other spins with an effective magnetic field.

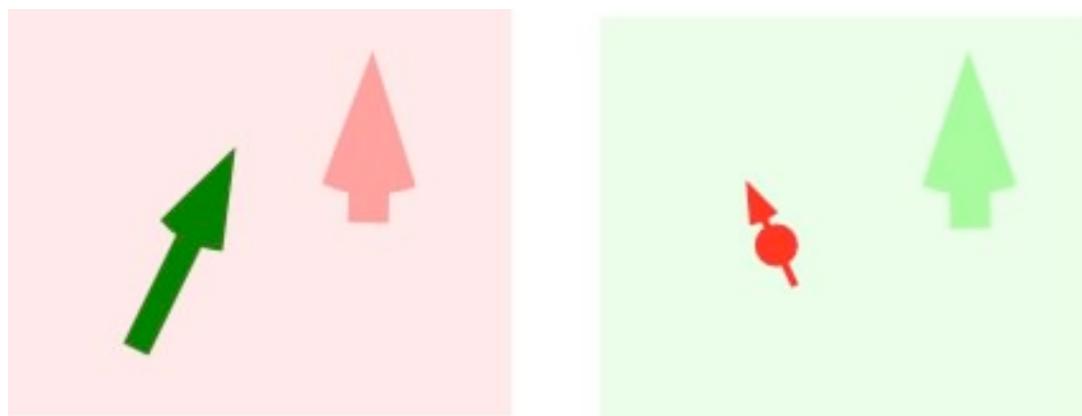

Self-consistent equations at $T=T_c$

$$\langle S_z \rangle = n_I \frac{S(S+1)}{3kT_c} J \langle s_z \rangle$$

$$\langle s_z \rangle = \left[\frac{\chi_P}{(g^* \mu_B)^2} \right] J \langle S_z \rangle$$



$$\langle S_z \rangle = \chi_C H = n_I \frac{S(S+1)}{3kT} g \mu_B H$$

$$\langle s_z \rangle = \chi_P h = \left[\frac{\chi_P}{(g^* \mu_B)^2} \right] g^* \mu_B h$$

The spin polarizations of Mn ions and **itinerant holes** under external magnetic field are described by **Curie** and **Pauli** susceptibilities.

$$kT_c = \frac{S(S+1)}{3} J^2 n_I \left[\frac{\chi_P}{(g^* \mu_B)^2} \right]$$

BUILDING SPIN-WAVE THEORY

Why Spin-Wave Theory?

Spin-wave theory -> the spatial fluctuations are inevitable once the $SU(2)$ continuous symmetry is spontaneously broken.


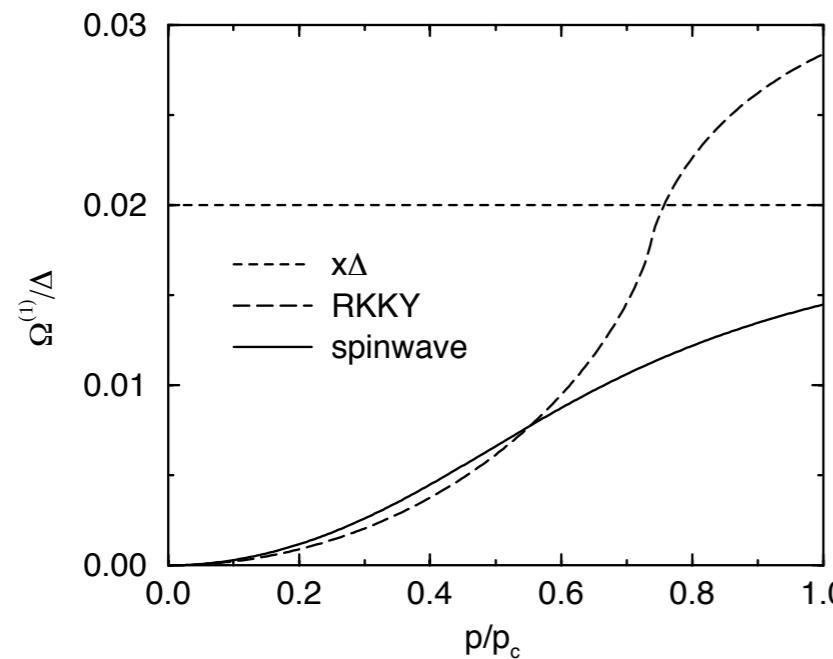


FIG. 1. Spin-wave dispersion for $c^* = 0.1 \text{ nm}^{-3}$. The short wavelength limit is the mean-field result $x\Delta$. For comparison, we show also the result obtained from an RKKY picture.

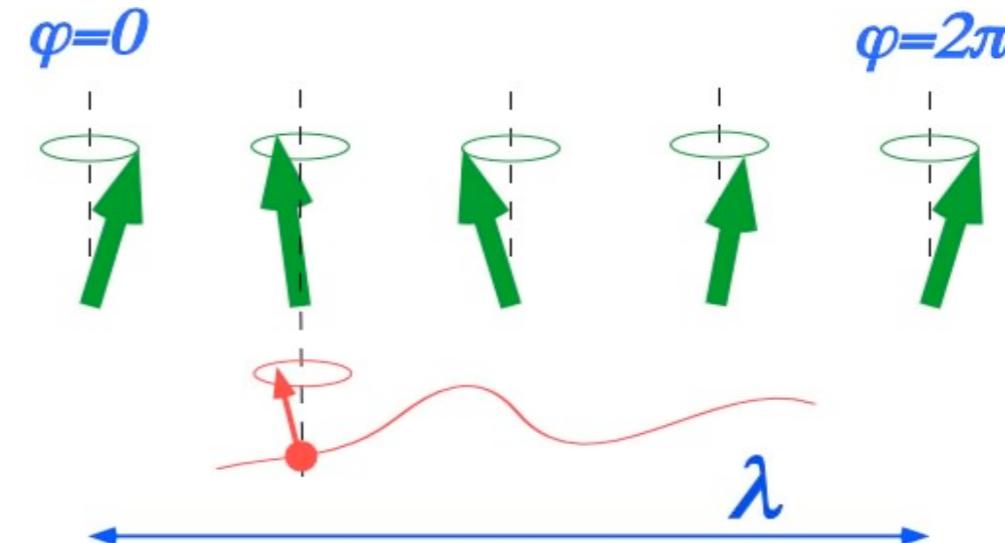

$$D^{-1}(\vec{p}, \Omega) = -i\Omega + g\mu_B B + J\langle s_z \rangle + \frac{n_I J^2 S}{2\beta V} \sum_{\vec{k}, \nu} G_{\uparrow}^{MF}(\vec{k}, \nu) G_{\downarrow}^{MF}(\vec{k} + \vec{p}, \nu + \Omega)$$

To include the spatial fluctuations, one needs to compute the spin-wave propagator D and the dispersion can be extracted from its pole.

Holstein-Primakov Boson

The spin-flip interactions ($S^+ \sigma^- + S^- \sigma^+$) were totally ignored in Weiss mean-field theory and the predicted *gapless* spin-wave excitations by Goldstone theorem are killed.

Making use of the path integral formalism, we can develop a spin-wave theory for the impurity spins by integrating out the itinerant ones. *However, the spin operator inside the path integral has the annoying Berry phase.* Therefore, some tweaking is in order...

$$\begin{aligned} S^+(r) &= \sqrt{2n_IS - b^\dagger(r)b(r)} \ b(r), \\ S^-(r) &= b^\dagger(r)\sqrt{2n_IS - b^\dagger(r)b(r)}, \\ S^z(x) &= n_IS - b^\dagger(r)b(r). \end{aligned}$$

In above, we introduce the Holstein-Primakov boson $b^\dagger(r), b(r)$ to represent the coarse-grained impurity spin density $S(r)$.

Path Integral Formalism

Writing down the path integral for the HP bosons and the itinerant carriers,

$$\begin{aligned} Z &= \int D[\bar{z}z] \int D[\bar{\psi}\psi] e^{-S[\bar{\psi}\psi, \bar{z}z]}, \\ &= \int D[\bar{z}z] \int D[\bar{\psi}\psi] e^{-\int_0^\beta d\tau \int d^3r \mathcal{L}[\bar{\psi}\psi, \bar{z}z]} \end{aligned}$$

where $\mathcal{L} = \sum_\sigma [\bar{\psi}_\sigma(r, \tau) \partial_\tau \psi_\sigma(r, \tau) + \bar{z}(r, \tau) \partial_\tau z(r, \tau)] + H[\bar{\psi}\psi, \bar{z}z]$ is the Lagrangian density in the imaginary-time formalism.

Separating the action into two parts $S = S_z + S_\psi$,

$$\begin{aligned} S_z &= \int d\tau \int d^3r \bar{z}(r, \tau) \partial_\tau z(r, \tau), \\ S_\psi &= \int d\tau \int d^3r \int d\tau' \int d^3r' \bar{\psi}(r, \tau) G^{-1}(r, \tau; r', \tau') \psi(r', \tau'), \end{aligned}$$

with

$$G^{-1} = \left(\partial_\tau - \frac{\nabla^2}{2m^*} - \mu + \frac{J}{2} \mathbf{S}(\bar{z}z) \cdot \boldsymbol{\tau} \right) \mathbf{1},$$

where the short-hand notation is used, $\mathbf{1} = \delta(\tau - \tau') \delta^3(r - r')$.

Integrating Out Itinerant Carriers

Since the action is quadratic in $\bar{\psi}\psi$, we can integrate out the itinerant carriers,

$$\begin{aligned} Z &= \int D[\bar{z}z] e^{-S_z[\bar{z}z]} \int D[\bar{\psi}\psi] e^{-S_\psi[\bar{\psi}\psi\bar{z}z]} \\ &= \int D[\bar{z}z] e^{-S_z} \det G^{-1}(\bar{z}z) = \int D[\bar{z}z] e^{-S_{\text{eff}}[\bar{z}z]}, \end{aligned}$$

where $S_{\text{eff}}[\bar{z}z] = \left[\int d\tau \int d^3r \bar{z}(r, \tau) \partial_\tau z(r, \tau) \right] - \ln \det G^{-1}(\bar{z}z)$ is the effective action for the HP bosons.

Split G^{-1} into G_0^{-1} (z -independent) and δG^{-1} (z -dependent) parts,

$$\begin{aligned} G_0^{-1} &= \left(\partial_\tau - \frac{\nabla^2}{2m^*} - \mu + \frac{\Delta}{2} \tau^z \right) \mathbf{1}, \\ \delta G^{-1} &= \frac{J}{2} \sqrt{2n_IS} (z\tau^- + \bar{z}\tau^+) - \frac{J}{2} \bar{z}z\tau^z, \end{aligned}$$

where $\Delta = Jn_IS$ is the Zeeman splitting at zero temperature.

Expanding the Series...

Making use of the following identity to expand the determinant,

$$\begin{aligned}\ln \det G^{-1} &= \text{tr} \ln G^{-1} = \text{tr} \ln(G_0^{-1} + \delta G^{-1}) \\ &= \text{tr} \ln G_0^{-1} + \text{tr} \ln(1 + G_0 \delta G^{-1}) \\ &= \text{tr} \ln G_0^{-1} - \text{tr} \sum_{n=1}^{\infty} (-G_0 \delta G^{-1})^n.\end{aligned}$$

Since δG^{-1} is at least linear in z , if we are interested in the quadratic terms of \bar{z}, z (that is, **Contribute only to specific heat**), we can truncate the series after the second term,

Weiss mean-field theory

$$S_{\text{eff}}[z] = -\frac{1}{2} \text{tr} \left[\frac{1}{2} \text{tr} (G_0 \delta G^{-1} G_0 \delta G^{-1}) \right]$$

leaving out the spin-wave interactions from higher order terms.

Crucial for spin-wave propagation

Spin-Wave Propagator (I)

The first term gives the same result as in Weiss MFT,

$$\begin{aligned} -\text{tr}(G_0 \delta G^{-1}) &= \frac{J}{2} \int d\tau \int d^3r \sum_{\sigma} \sigma G_0^{\sigma}(r, \tau; r, \tau^+) \bar{z}(r, \tau) z(r, \tau) \\ &= \frac{J}{2} (n_{\downarrow} - n_{\uparrow}) \int d\tau \int d^3r \bar{z}(r, \tau) z(r, \tau). \end{aligned}$$

To go from the first to the second line, we recall the definition that $G_0^{\sigma}(r, \tau; r, \tau^+) = \langle T\psi_{\sigma}(r, \tau)\psi_{\sigma}^{\dagger}(r, \tau^+) \rangle = -\langle \psi_{\sigma}^{\dagger}(r, \tau)\psi_{\sigma}(r, \tau) \rangle = -n_{\sigma}$. The second term is slightly more complicated,

$$\begin{aligned} \frac{1}{2} \text{tr}(G_0 \delta G^{-1} G_0 \delta G^{-1}) &= \frac{n_I J^2 S}{2} \int d\tau \int d^3r \int d\tau' \int d^3r' \\ &\quad G_0^{\uparrow}(r, \tau; r', \tau') \bar{z}(r', \tau') G_0^{\downarrow}(r', \tau'; r, \tau) z(r, \tau). \end{aligned}$$

Collecting both contributions, the spin-wave propagator is

$$D^{-1}(r', \tau'; r, \tau) = (\partial_{\tau} + \frac{J n_h \alpha_h}{2}) \mathbf{1} + \frac{n_I J^2 S}{2} G_0^{\uparrow}(r, \tau; r', \tau') G_0^{\downarrow}(r', \tau'; r, \tau).$$

Spin-Wave Propagator (II)

Or, the propagator would look more familiar in momentum space,





$$D(p, \nu_n) = \frac{-1}{i\nu_n - \Sigma_W - \Sigma_{sw}(p, \nu_n)},$$

where the self energy corrections from integrating out the itinerant carriers are,

$$\begin{aligned}\Sigma_W &= \frac{1}{2} J n_h \alpha_h = J \langle \sigma^z \rangle, \\ \Sigma_{sw}(p, \nu_m) &= \frac{n_I J^2 S}{2\beta} \sum_m \int \frac{d^3 k}{(2\pi)^3} G_0^\uparrow(k, \omega_n) G_0^\downarrow(k + p, \omega_m + \nu_n).\end{aligned}$$

Note that, the constant part of the self energy Σ_W is the same as the Weiss mean-field theory at low temperatures, while $\Sigma_{sw}(p, \nu_n)$ carries frequency dependency, implying that there are *more than one collective excitations*.


Collective Excitations

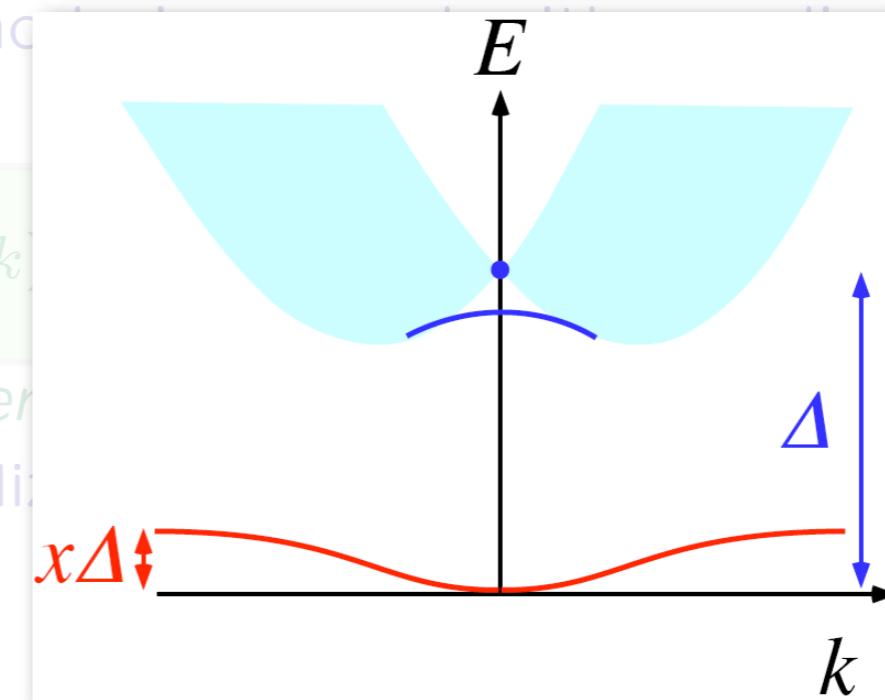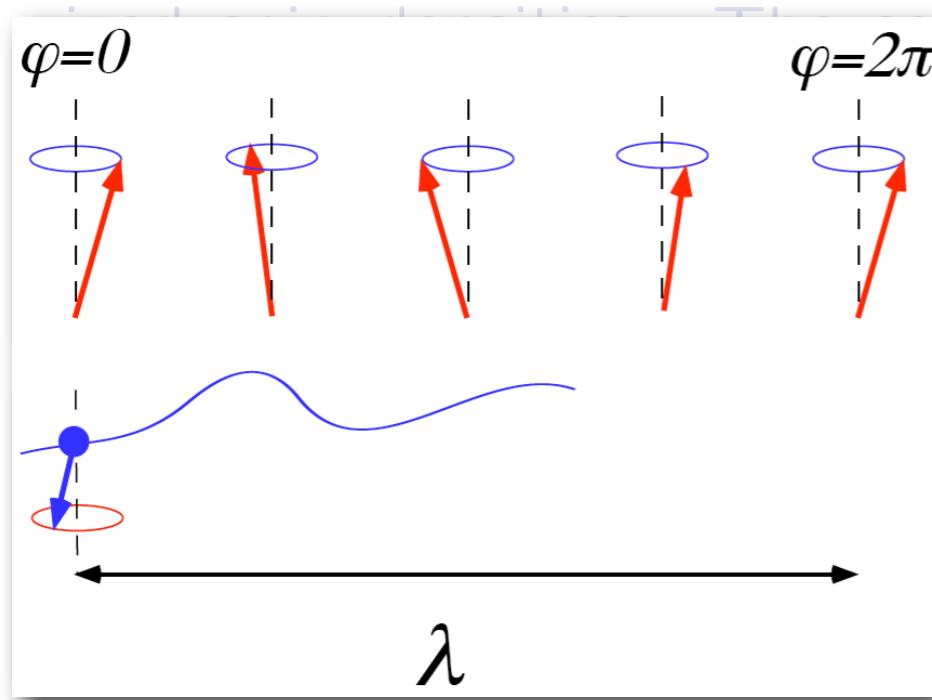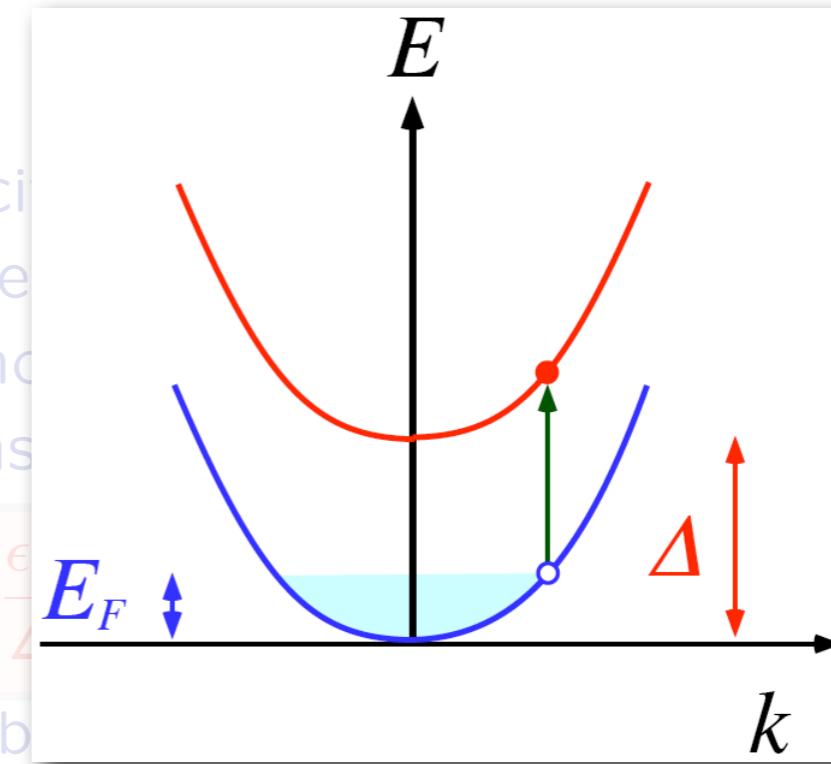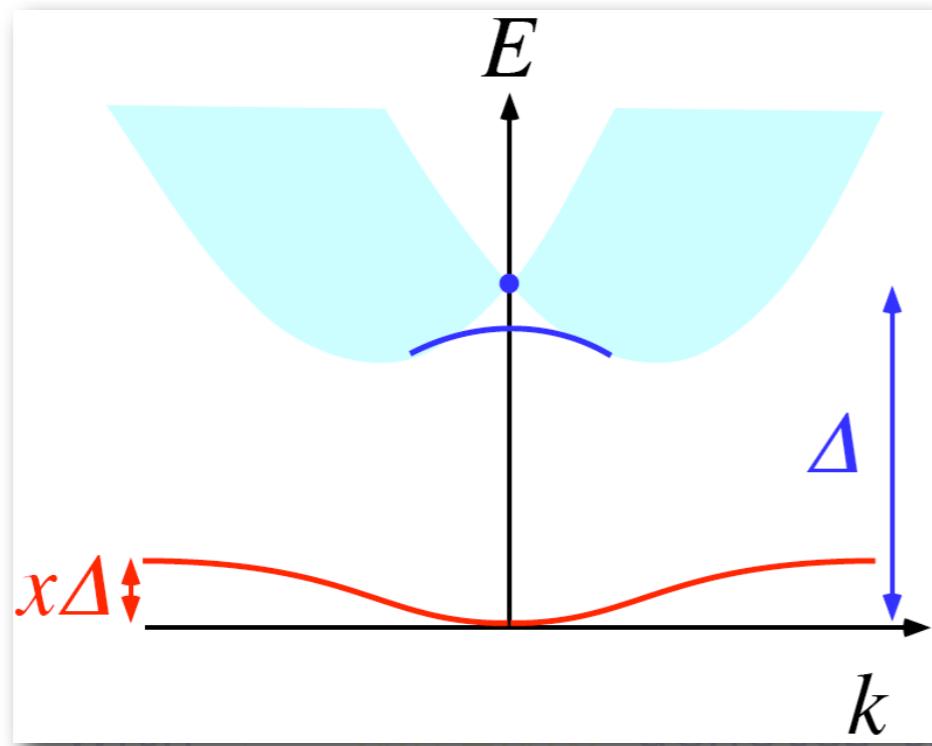


SPIN WAVE RELAXATION

Transport Property

MacDonald et al.
Nature Materials 4, 195 (2005)

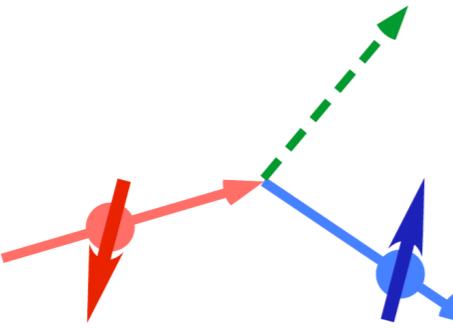

The conventional mean-field theory neglects the scattering between electronic magnons and spin waves. In order to address the transport issues, Green's function approach is necessary!!

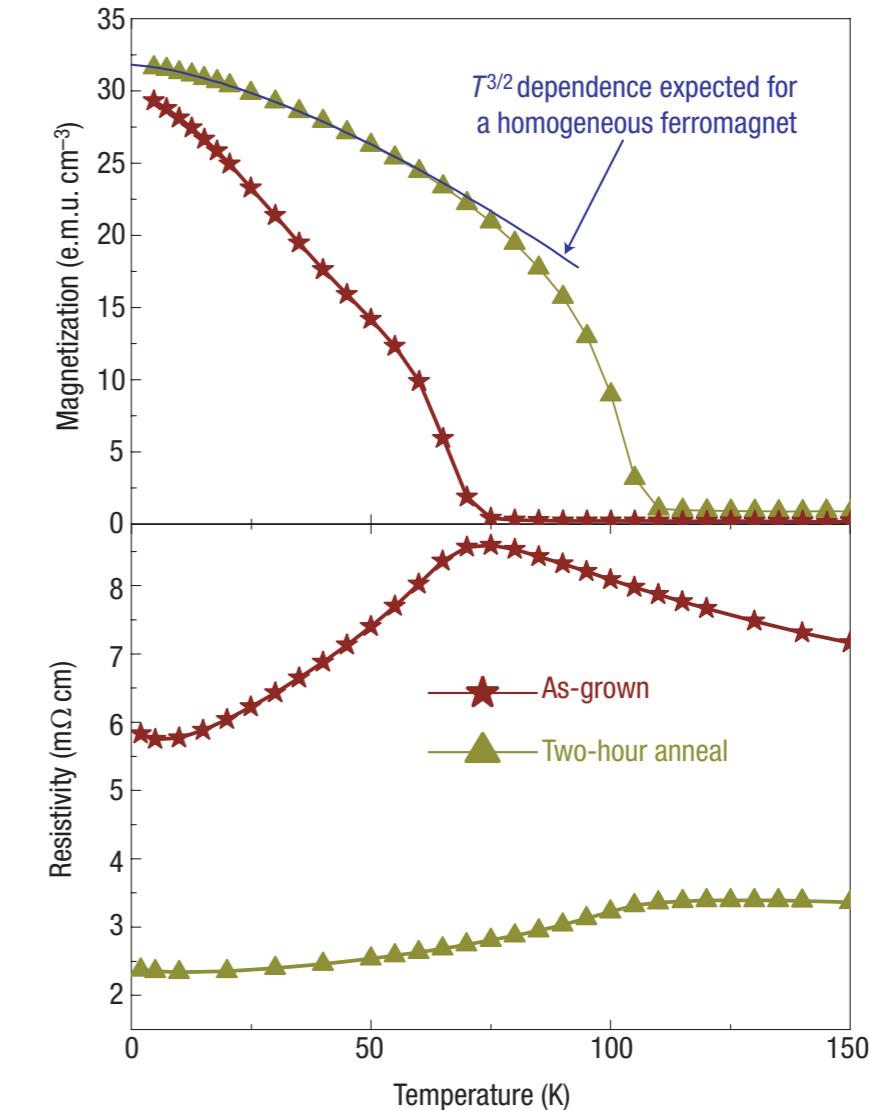

What is the origin of the resistivity peak around the Curie temperature?

Green's Function Approach

- (1) We start with the Zener model but keep **both** the itinerant and impurity spins.
- (2) To describe the correlations between itinerant and impurity spins, we introduce the Green's functions:

$$D(r_1, r_2; t) \equiv \langle\langle S^+(r_1, t); S^-(r_2, 0) \rangle\rangle$$

$$F(r_1, r'_1, r_2; t) \equiv \langle\langle \psi_\uparrow^\dagger(r_1, t) \psi_\downarrow(r'_1, t); S^-(r_2, 0) \rangle\rangle.$$

- (3) Writing down the dynamical equations for the Green's function self-consistently.
- (4) Solve the coupled differential equations and compute interested physical quantities, such as magnetization, spin-wave relaxation rate and so on.

Definition of Green's Function

The Green's function approximates a spin wave at $r=r_2$ and $t=0$, then does not approximate : annihilating it at $r=r_1$ in later time t . function for the impurity spins is defined by

$$D(r_1, r_2; t) \equiv \langle\langle S^+(r_1, t); S^-(r_2, 0) \rangle\rangle$$

It describes the correlation of creating a spin wave at $r=r_2$ and $t=0$, then annihilate an electronic magnon (particle-hole pair) at $r=r_1$, $r=r_1'$ in later time t .

$$S^-(r_2, 0)S^+(r_1, t)\rangle.$$

Self-consistency, it is a function which describes the correlation between impurity and itinerant spins,

$$F(r_1, r'_1, r_2; t) \equiv \langle\langle \psi_\uparrow^\dagger(r_1, t)\psi_\downarrow(r'_1, t); S^-(r_2, 0) \rangle\rangle.$$

Time Evolution

Taking time derivative of the Green's function $D(r_1, r_2; t)$,

$$\begin{aligned} i \frac{\partial D}{\partial t} &= \delta(t) \langle S^+(r_1, 0) S^-(r_2, 0) \rangle + \Theta(t) \langle \frac{dS^+(r_1, t)}{dt} S^-(r_2, 0) \rangle \\ &\quad - \delta(t) \langle S^-(r_2, 0) S^-(r_1, 0) \rangle + \Theta(t) \langle S^-(r_2, 0) \frac{dS^+(r_1, t)}{dt} \rangle \\ &= \delta(t) \left\langle [S^+(r_1, 0), S^-(r_2, 0)] \right\rangle + i \left\langle \left\langle \frac{dS^+(r_1, t)}{dt}; S^-(r_2, 0) \right\rangle \right\rangle. \end{aligned}$$

The first term consists of the equal-time commutator and can be easily calculated,

$$\delta(t) \langle [S^+(r_1, 0), S^-(r_2, 0)] \rangle = \delta(t) \delta^3(r_1 - r_2) \langle S^z(r_1) \rangle.$$

As for the second term, we need to derive the Heisenberg equation of the spin operator $S^+(r_1, t)$.

Heisenberg Equations

The time evolution of the spin operator $S^+(r_1, t)$ is,

$$i \frac{dS^+(r_1, t)}{dt} = [S^+(r_1, t), H] = [S^+(r_1, t), H_{ex}],$$

since the kinetic energy of the itinerant carriers is independent of the impurity spin and thus does not contribute.

$(J/2)S^+\sigma^-)S^-\sigma^+$ composed into three terms, zero and the dynamics is described by the remaining two terms,

$$i \frac{dS^+(r_1, t)}{dt} = JS^z (-JS^+(r_1, t)\sigma^z(r_1, t))$$

Now we are ready to put the operator back into the correlator.

Mean-Field Decomposition

Finally, we get the last piece of the puzzle,

$$\begin{aligned} & i \left\langle \left\langle \frac{dS^+(r_1, t)}{dt}; S^-(r_2, 0) \right\rangle \right\rangle \\ &= J \left\langle \left\langle S^z(r_1, t) \sigma^+(r_1, t); S^-(r_2, 0) \right\rangle \right\rangle - J \left\langle \left\langle \sigma^z(r_1, t) S^+(r_1, t); S^-(r_2, 0) \right\rangle \right\rangle, \\ & \approx J \langle S^z(r_1) \rangle \left\langle \left\langle \sigma^+(r_1, t); S^-(r_2, 0) \right\rangle \right\rangle - J \langle \sigma^z(r_1) \rangle \left\langle \left\langle S^+(r_1, t); S^-(r_2, 0) \right\rangle \right\rangle, \\ &= J \langle S^z(r_1) \rangle F(r_1, r_1, r_2; t) - J \langle \sigma^z(r_1) \rangle D(r_1, r_2; t). \end{aligned}$$

Since the mean-field approximation is carried out at the level of **equations of motion** (not at the Hamiltonian level, as in Weiss mean-field theory), *it captures the correct spin kinematics and also includes the spatial fluctuations!!*

Self-Consistent EOM's

After some algebra, the self-consistent differential equations for the Green's functions are:

$$\begin{aligned} i\partial_t D(r_1, r_2; t) &= 2\langle S^z(r_1) \rangle \delta(t) \delta^3(r_1 - r_2) \\ &\quad - J\langle \sigma^z(r_1) \rangle D(r_1, r_2; t) \\ &\quad + J\langle S^z(r_1) \rangle F(r_1, r_1, r_2; t), \end{aligned}$$

$$\begin{aligned} i\partial_t F(r_1, r'_1, r_2; t) &= \left(\frac{\nabla_{r_1}^2}{2m^*} - \frac{J}{2} \langle S^z(r_1) \rangle \right) F(r_1, r'_1, r_2; t) \\ &\quad - \left(\frac{\nabla_{r'_1}^2}{2m^*} + \frac{J}{2} \langle S^z(r'_1) \rangle \right) F(r_1, r'_1, r_2; t) \\ &\quad - \frac{J}{2} \langle \psi_\downarrow^\dagger(r_1) \psi_\downarrow(r'_1) \rangle D(r_1, r_2; t) \\ &\quad + \frac{J}{2} \langle \psi_\uparrow^\dagger(r_1) \psi_\uparrow(r'_1) \rangle D(r'_1, r_2; t), \end{aligned}$$

Callen Formula

Yang, Chang and Sun pointed out that the spin-wave theory can be extended to finite temperature and the magnetization can be computed by the well-known **Callen formula**,

$$\langle S^z \rangle = cS - c\Phi + \frac{(2S+1)c}{[(1+\Phi)/\Phi]^{2S+1} - 1},$$

$$\langle S^z \rangle = c\{S - n(\Omega) + (2S+1)n[(2S+1)\Omega]\},$$

$$\Phi = \frac{1}{cV} \sum_p n(\Omega_p)$$

$$n(\Omega) \equiv \frac{1}{cV} \sum_p n(\Omega_p)$$

$$k_B T_c = \frac{S(S+1)/3}{\lim_{\langle S^z \rangle, n^* \rightarrow 0} (1/V) \sum_{|\vec{p}| < p_c} \langle S^z \rangle / \Omega_p c^2}.$$

Yang, Chang, Sun
Phys. Rev. Lett. 86, 5636 (2001)


Konig, Lin, MacDonald
Phys. Rev. Lett. 86, 5637 (2001)

We further notice that the connection to the conventional Weiss MFT is rather simple,


Estimate Curie Temperature?

To estimate the Curie temperature, it is crucially important to include the thermal fluctuations correctly. That is to say, one needs to respect the spin-wave kinematics:


$$EG_{ij}(E) = 2\lambda_i\delta_{ij} + \left(\sum_l J_{lj}\lambda_l \right) G_{ij}(E) - \epsilon \left[\lambda_i \sum_l J_{il}G_{lj}(E) \right]$$

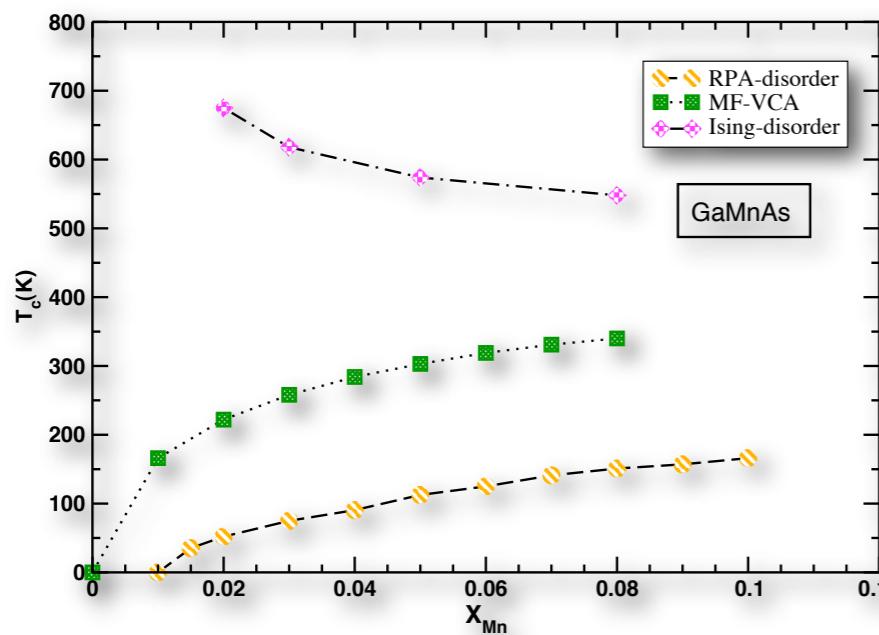

Bouzerar, Ziman, Kudrnovsky
Europhys. Lett. 69, 812 (2005)

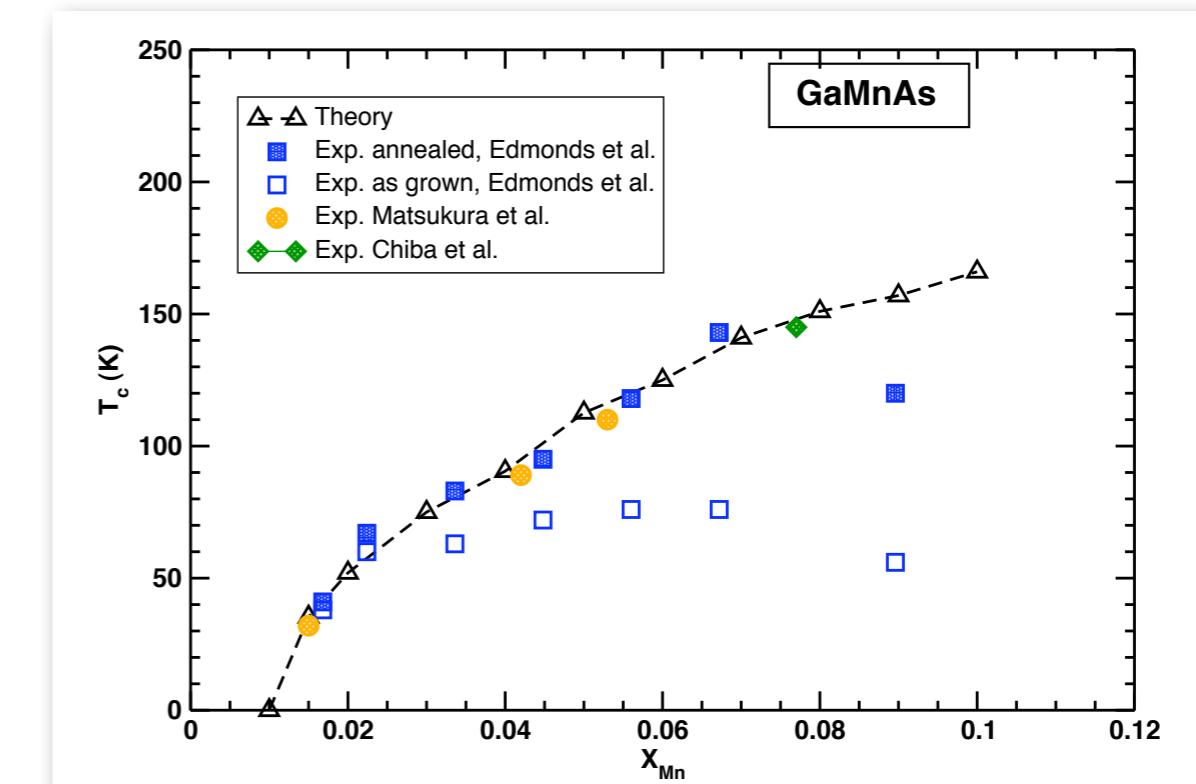

Spin-Wave Relaxation

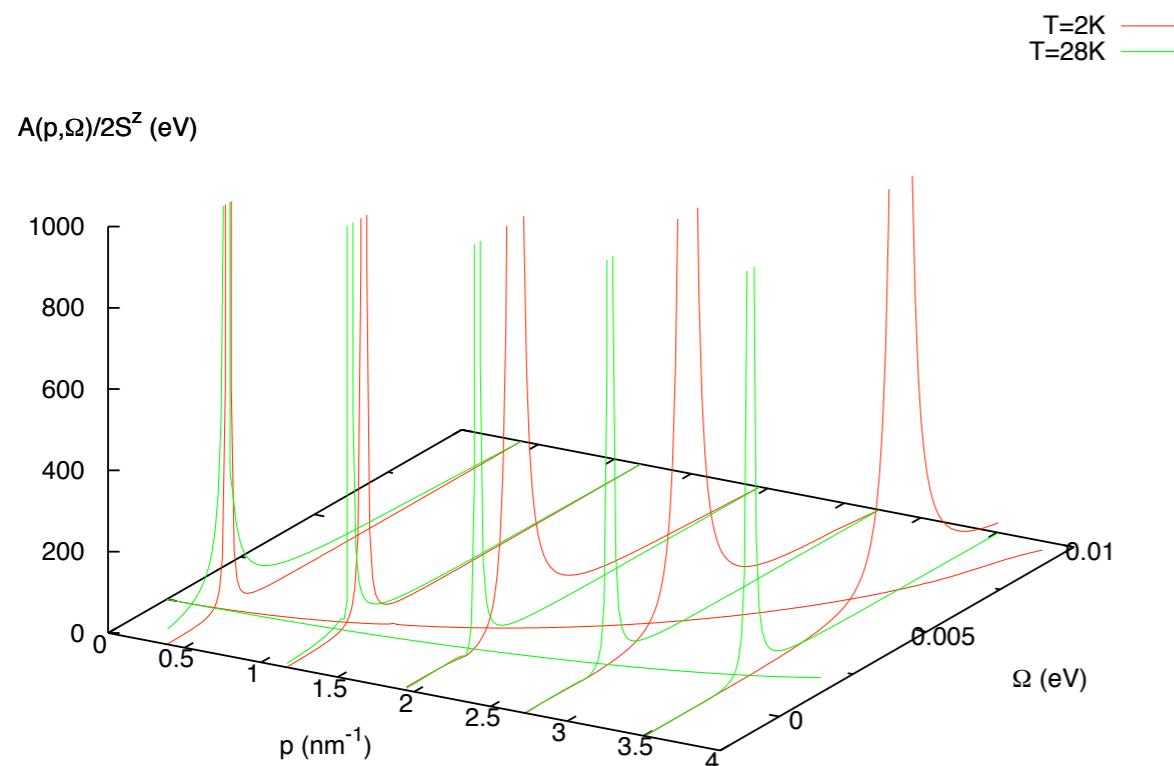


We can solve the spin-wave propagator first and compute its imaginary part to obtain the spin spectral function:

$$\begin{aligned} A(p, \omega) &= -\left(\frac{1}{\pi}\right) \text{Im}D(p, \Omega), \\ &= 2\langle S^z \rangle \left(\frac{Z}{\pi}\right) \frac{\Gamma(p)}{(\Omega - \omega_p)^2 + \Gamma(p)^2} \end{aligned}$$


- (1) The spin spectral function takes the Lorentzian shape with temperature-dependent halfwidth.
- (2) The spectral function actually **sharpens up** when T increases!!

Anomalous T dependence (I)

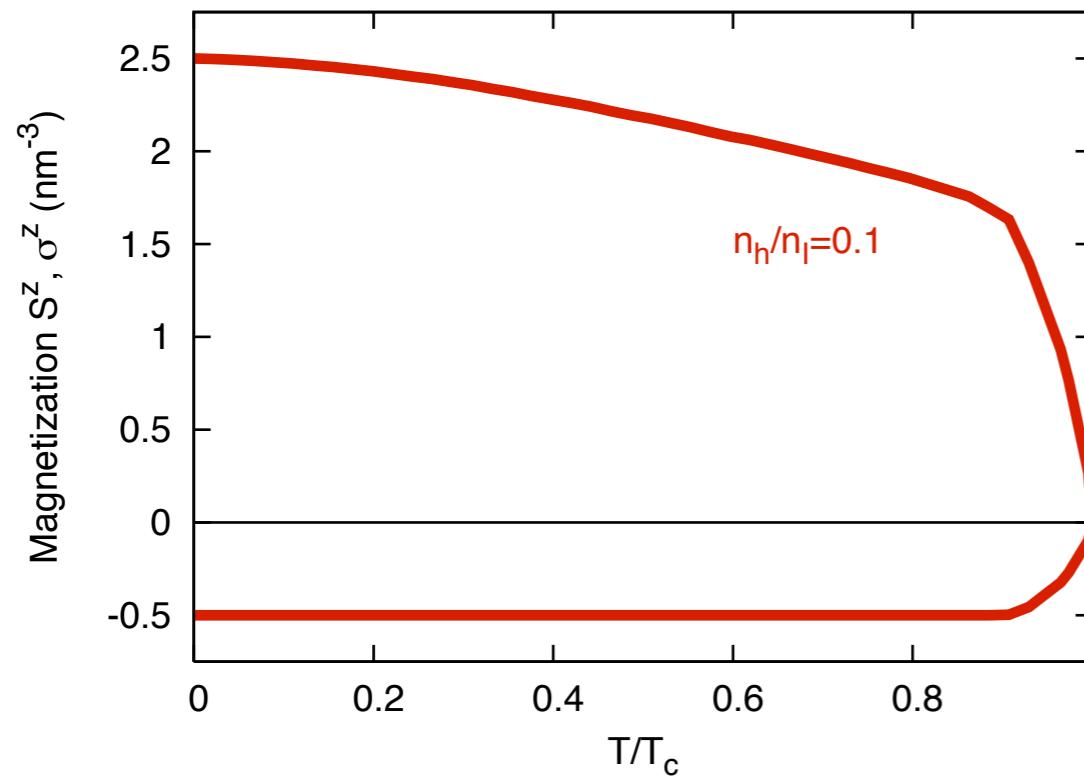


It is rather surprising that the spin-wave relaxation rate shows a significant peak around the Curie temperature!!

For the density ratio $n_h/n_l = 0.1$, the magnetization curve shows rather unusual shape compared with the conventional Brillouin function.

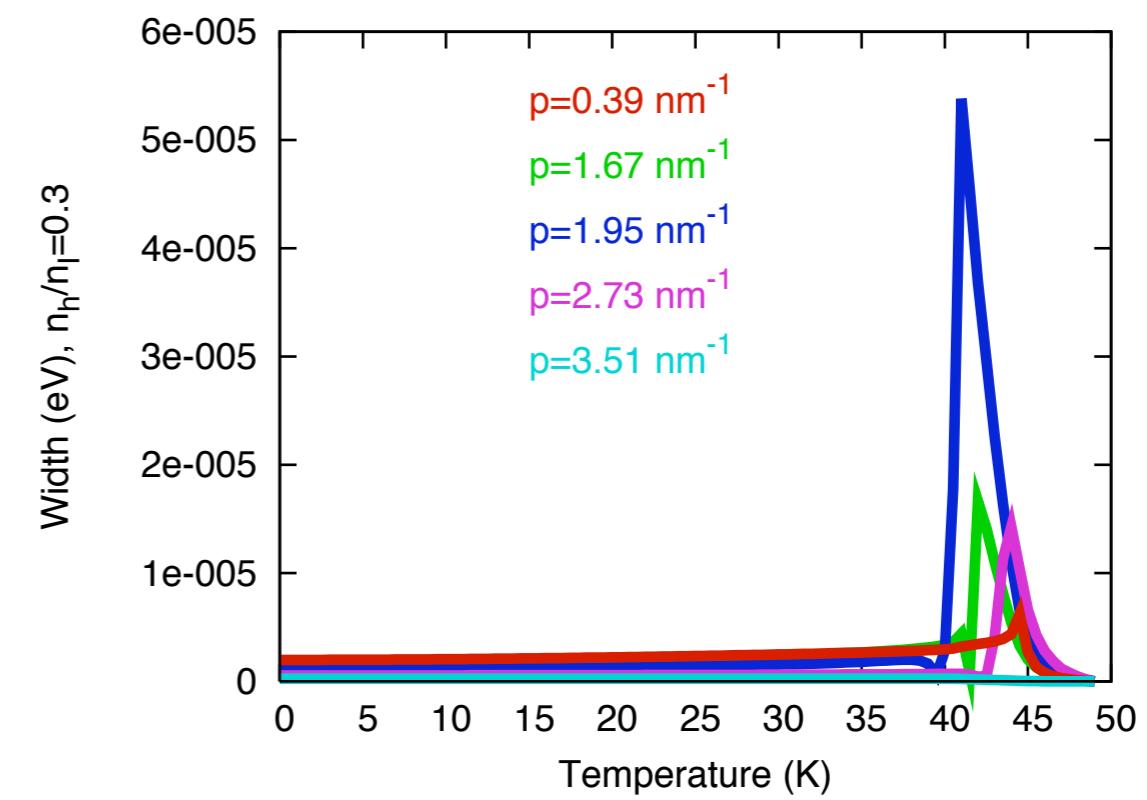


Anomalous T dependence (II)

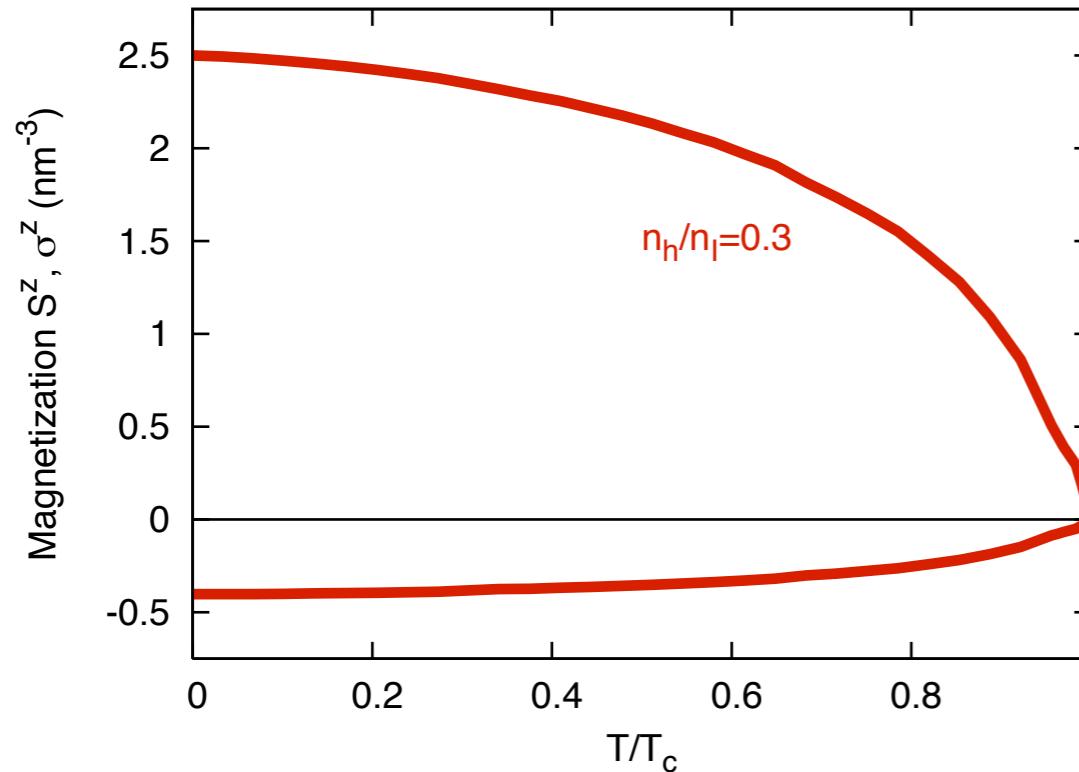


The peak near the Curie temperature disappears as well!!

For the density ratio $n_h/n_l = 0.3$, the magnetization curve becomes normal.

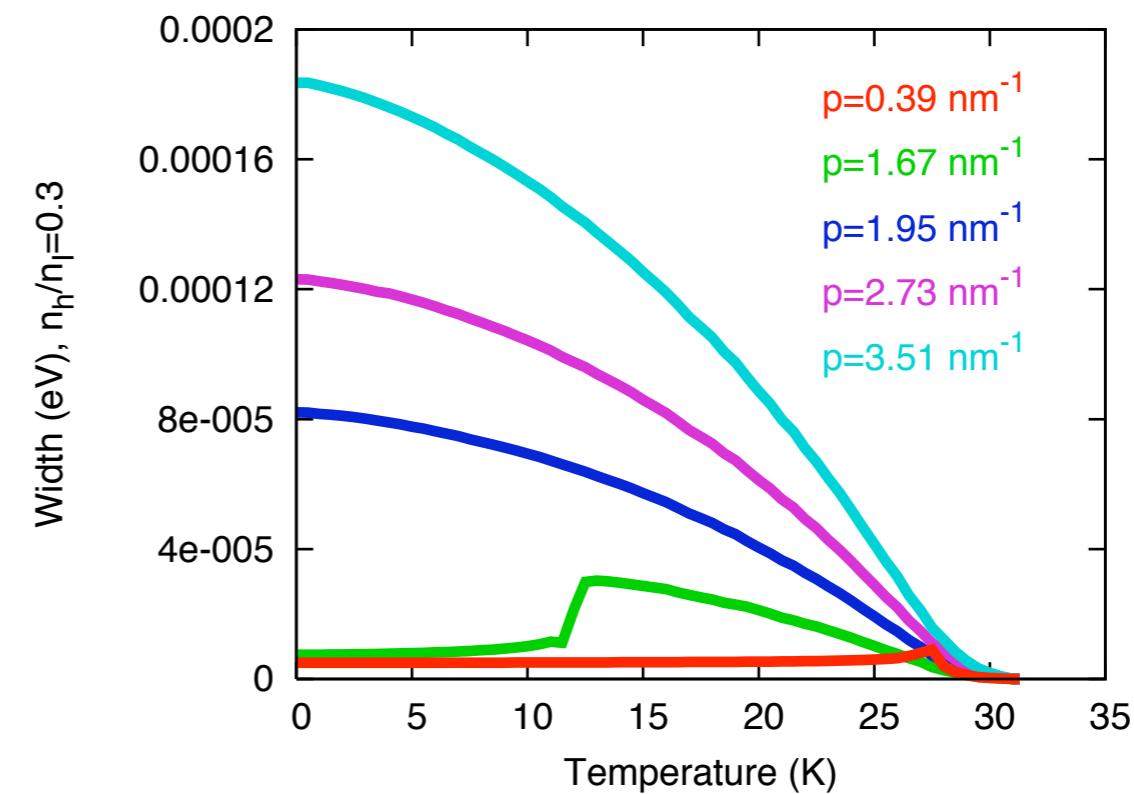

NON-COLLINEAR EXCHANGE COUPLING

Trilayer Magnetic Junction

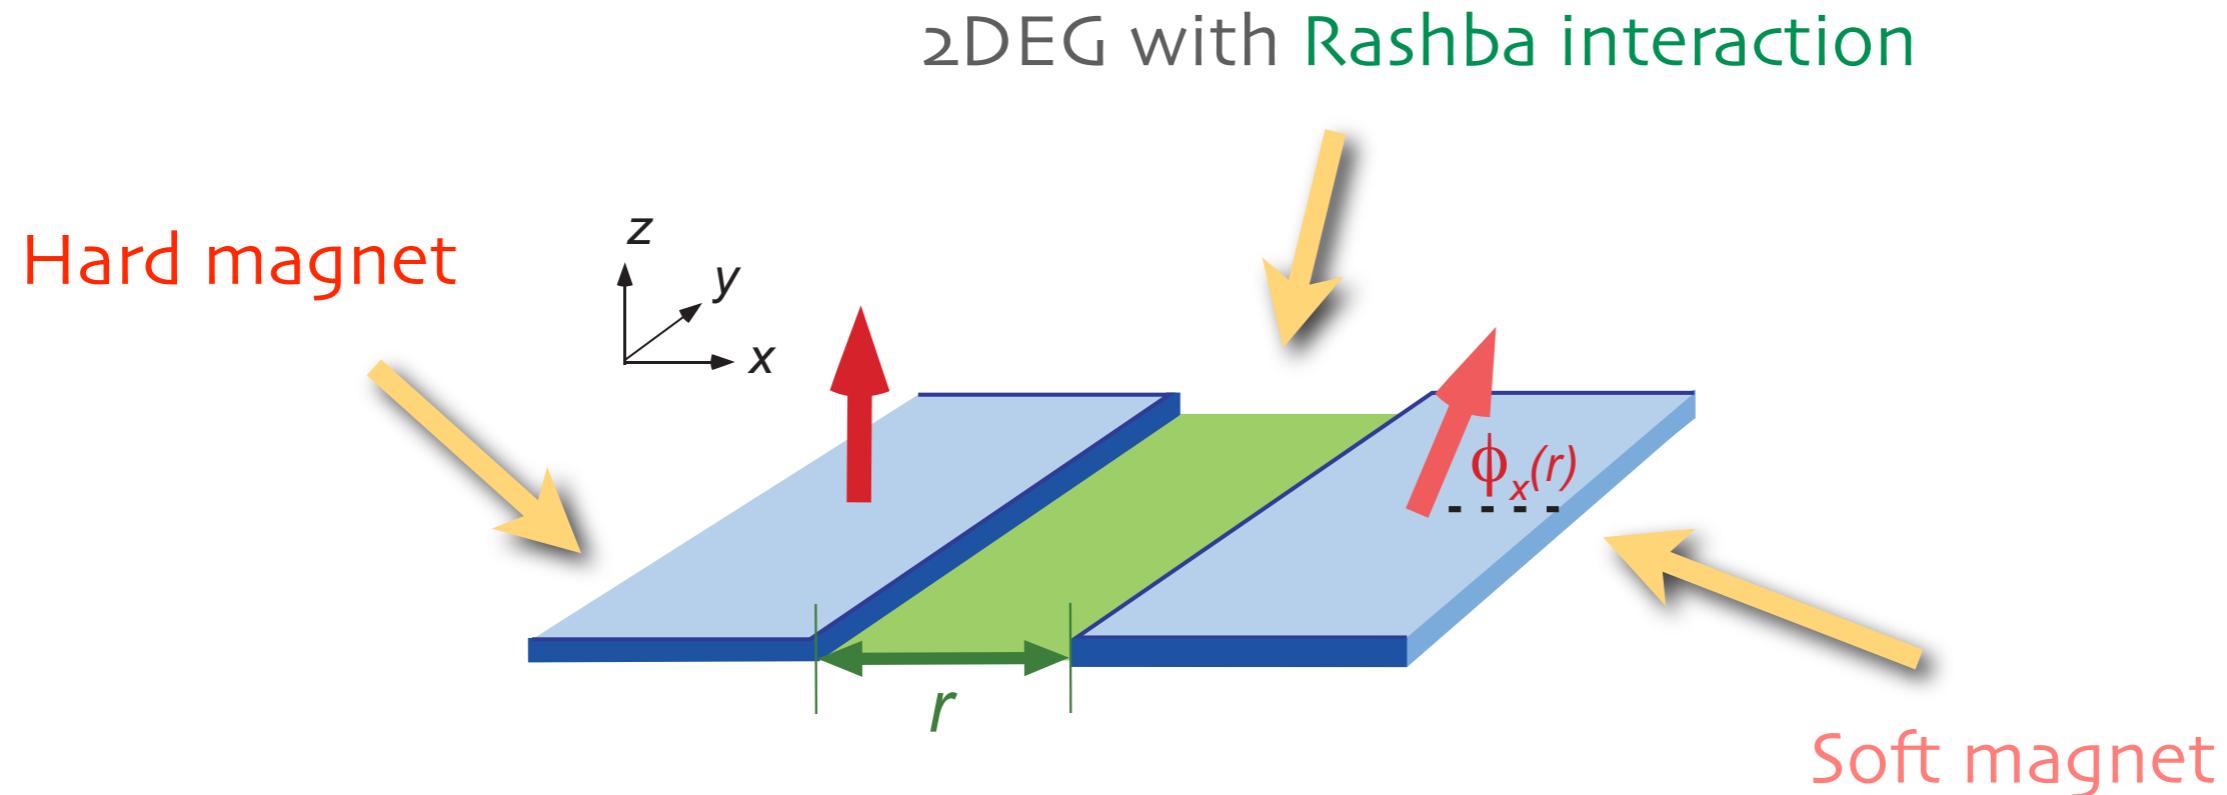


we model the intermediate layer by the Rashba Hamiltonian,

$$H = \int d^2r \Psi^\dagger \left[\frac{k^2}{2m^*} \mathbf{1} + \gamma_R (k_y \sigma^x - k_x \sigma^y) \right] \Psi,$$


where γ_R is the strength of the Rashba interaction.

Non-Collinear Spiral Angle?

Following Datta-Das' argument, the orientation of the spin will rotate along the effective B field with a **spiral angle** $\theta(d)$, where d is the width of the junction.

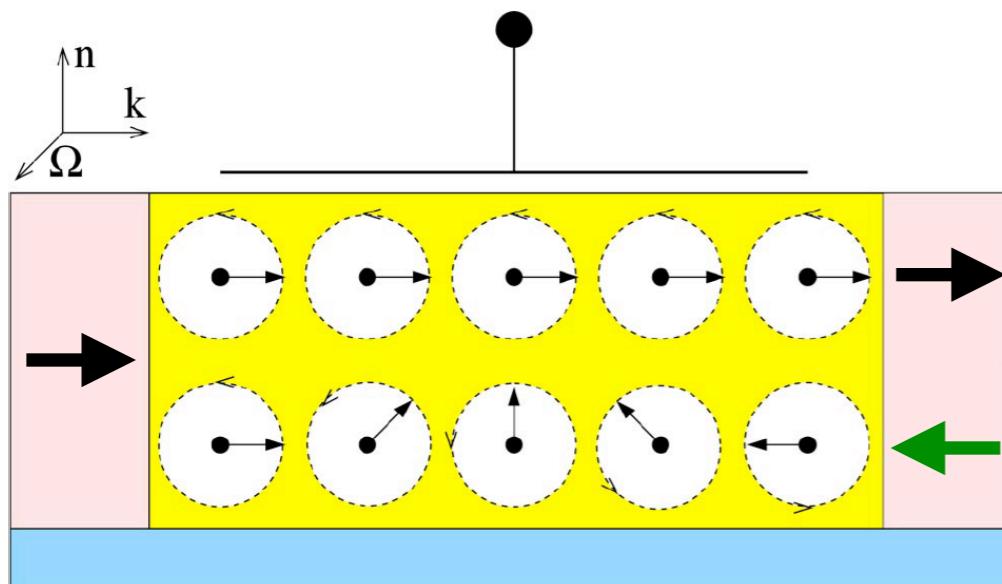



The spin of the itinerant carriers will align the soft magnet with the same spiral angle.

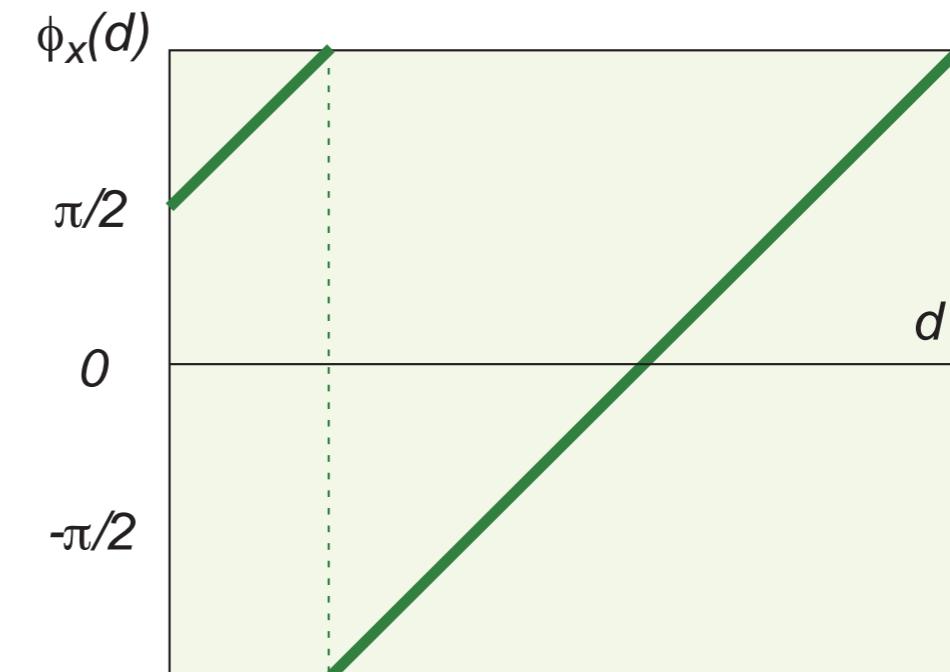

Therefore, we expect an effective **non-collinear** exchange coupling!

RKKY Instead?



BUT! Our conventional wisdom tells us that the mediated effective coupling is **collinear** RKKY interaction...

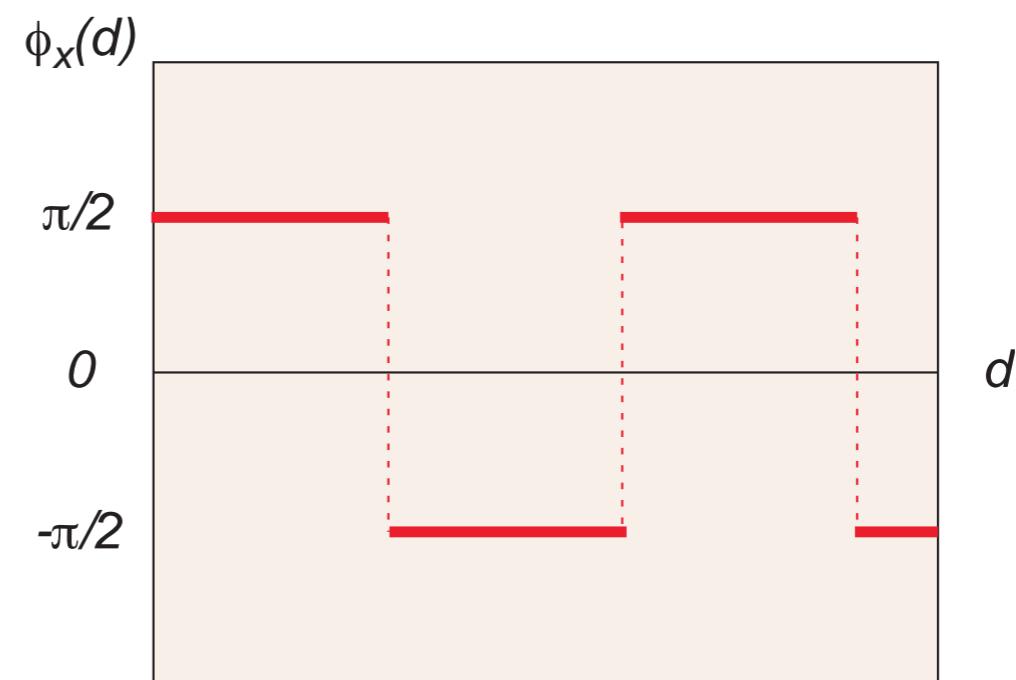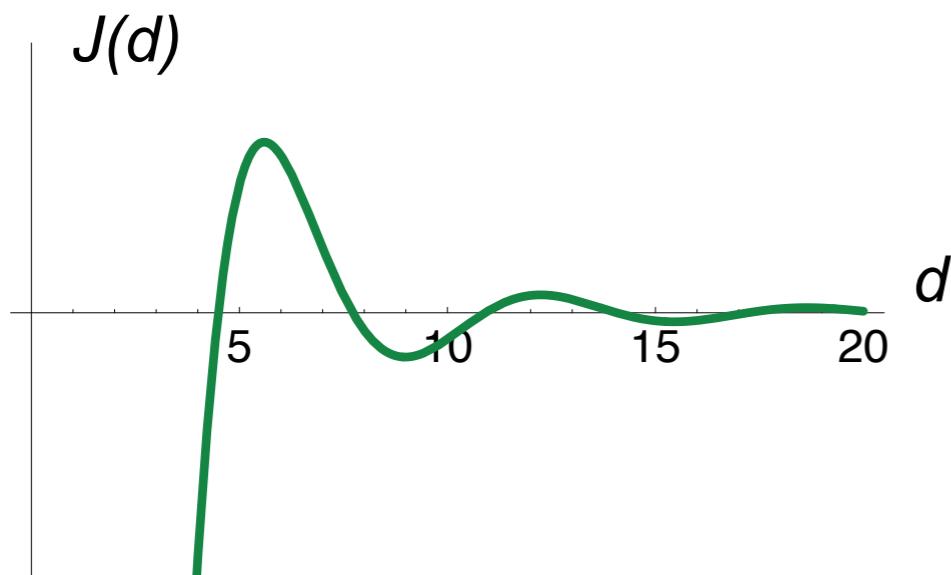

RKKY interaction:

It can be viewed as the quantum interferences due to patches of the Fermi surface related by the time-reversal symmetry.

Who's the Boss?

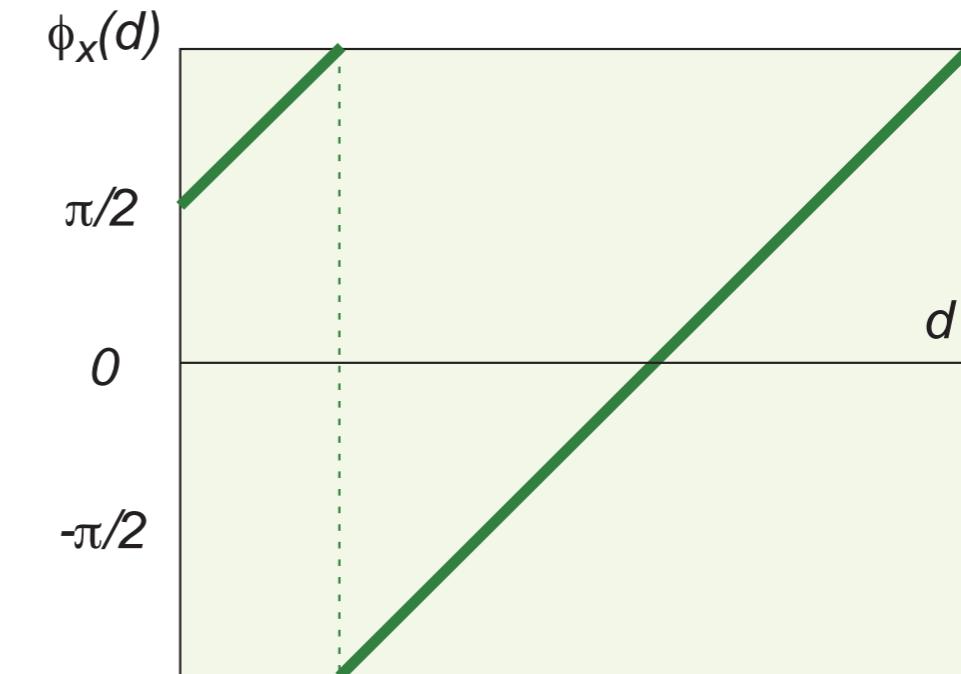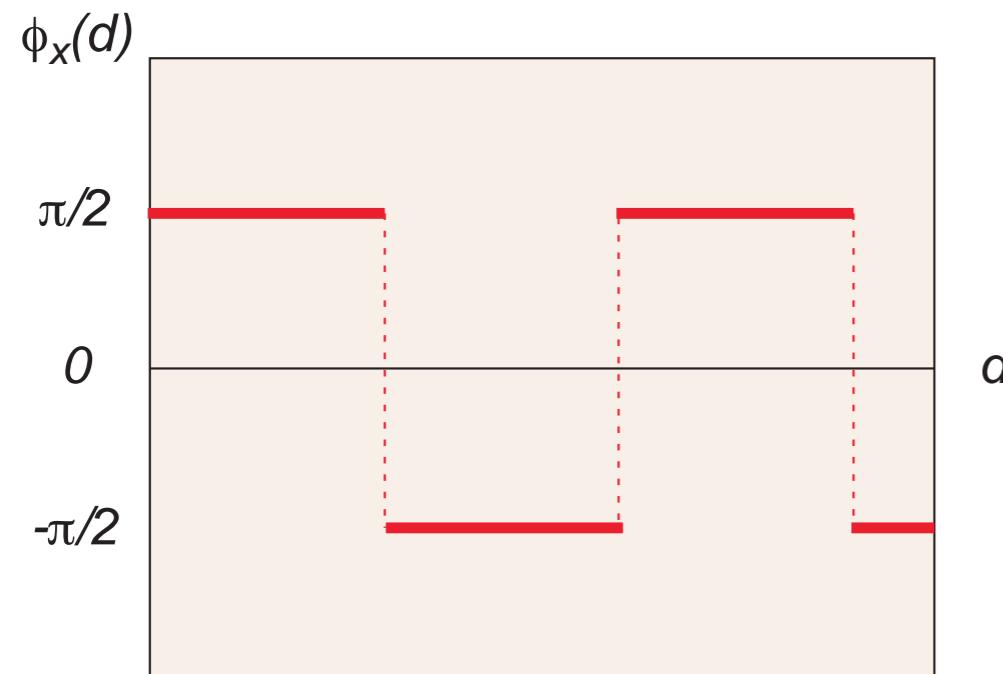

RKKY?


Spiral?

Chirality and Eigenstates

Due to the spin-orbital interaction, spin is no longer the good quantum number but replaced by the chirality instead,

$$\lambda = (\hat{\mathbf{k}} \times \hat{\mathbf{s}}) \cdot \hat{\mathbf{z}} = \pm 1.$$

It is important to remind the readers that, under the time reversal transformation, both momentum and spin reverse their directions and make the chirality invariant.

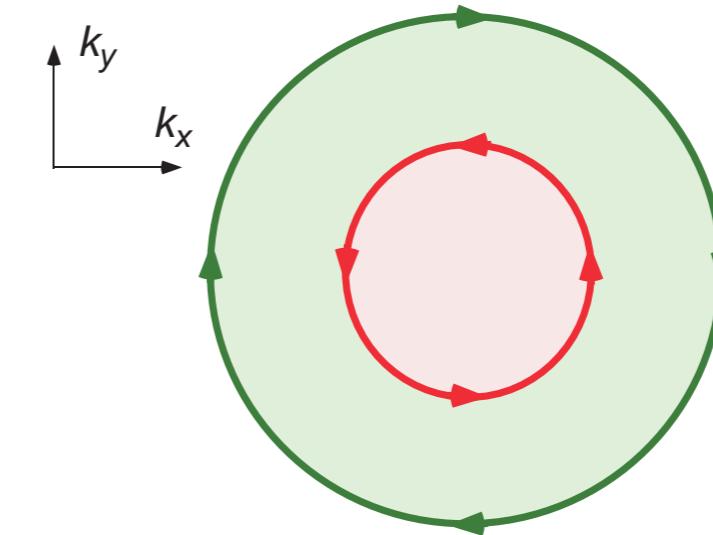


The Rashba Hamiltonian can be brought into its eigenbasis in momentum space,


$$\varphi_{k\lambda}(\vec{r}) = e^{i\vec{k} \cdot \vec{r}} u_\lambda(\phi) = \frac{e^{i\vec{k} \cdot \vec{r}}}{\sqrt{2}} \begin{pmatrix} -i\lambda e^{-i\theta_k} \\ 1 \end{pmatrix}$$

where $\theta_k = \tan^{-1}(k_y/k_x)$ with dispersion $\epsilon_{k\lambda} = k^2/2m^* - \lambda\gamma_R k$.

Weak Rashba Regime

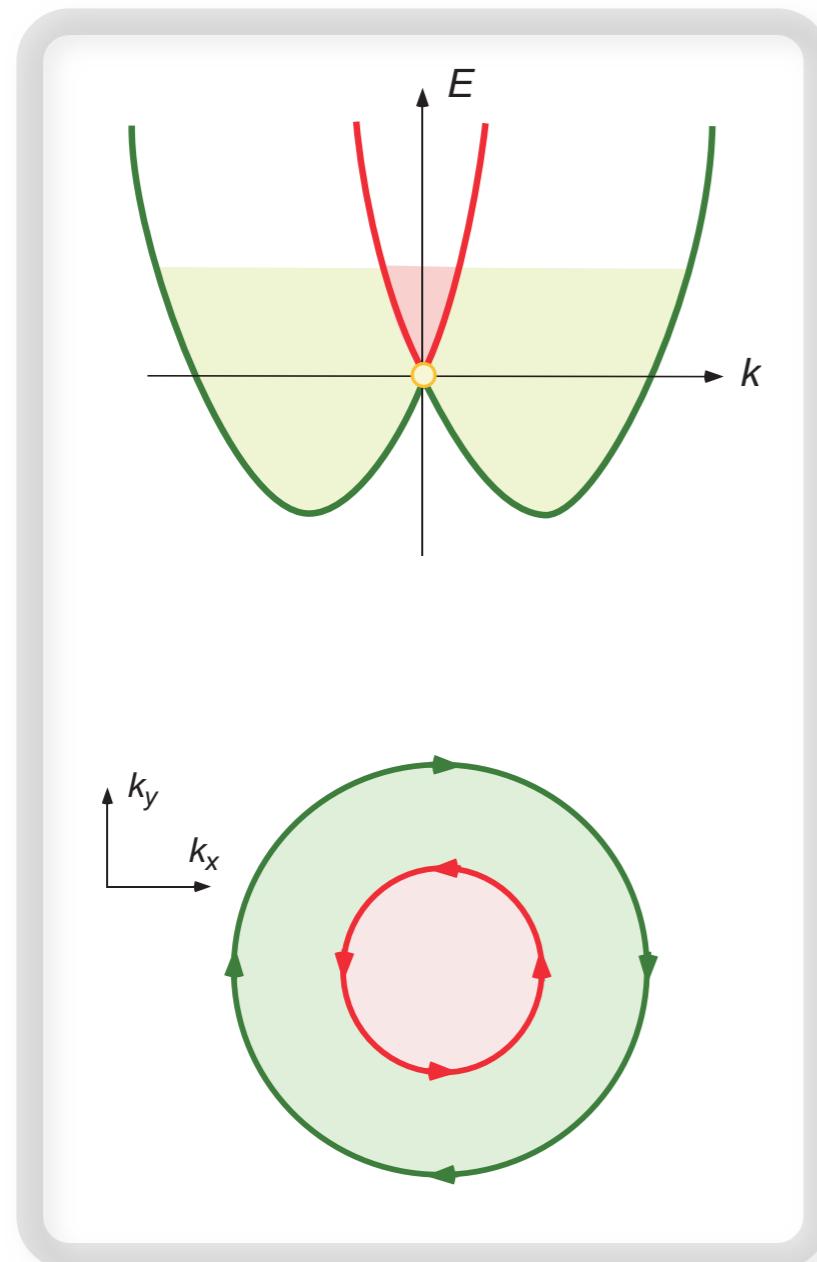



When Rashba coupling is small (compared with the Fermi energy), the Fermi surfaces consist of **two particle-like circles with opposite chiralities**.

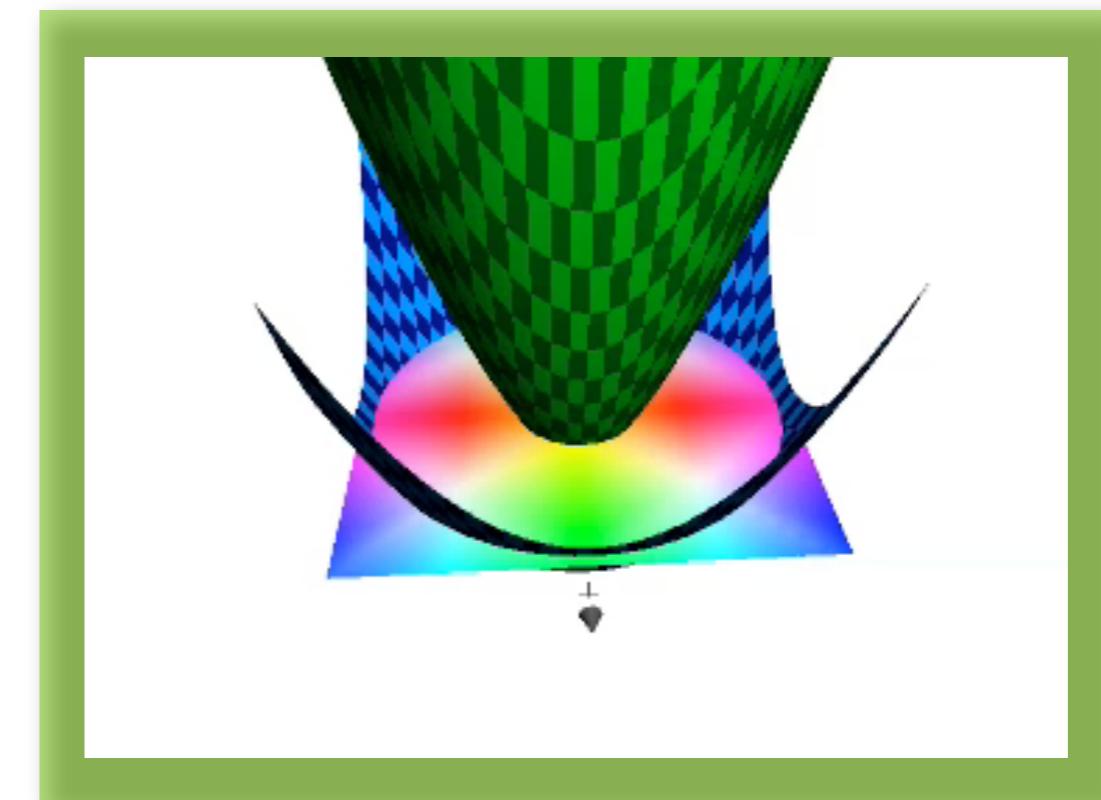

Weak Rashba regime with $\Delta_R/\epsilon_F < 1$


Dilute Density Regime

When the Fermi energy is small, the Fermi surfaces consist of **one particle-like and one hole-like circles with the same chiralities**.

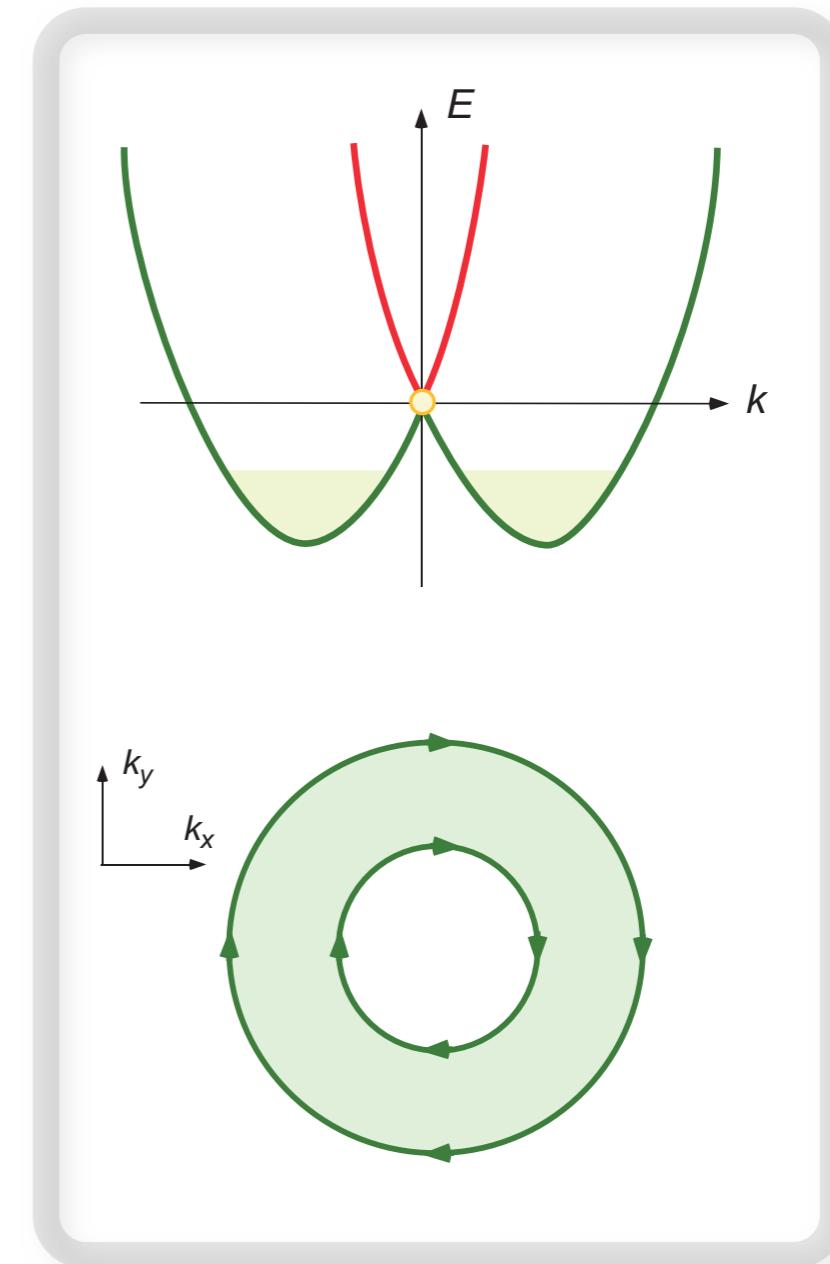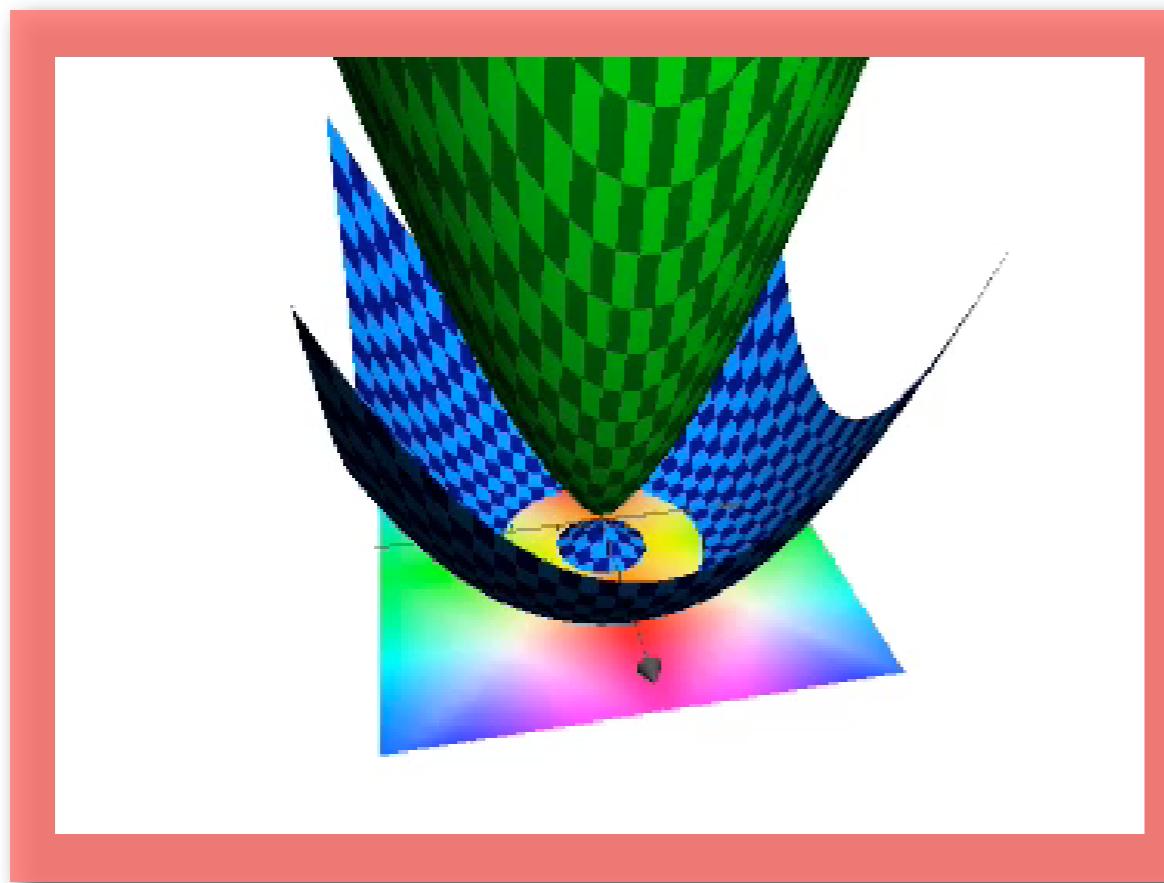

Dilute density regime with $\Delta_R/\epsilon_F > 1$


Numerical Results

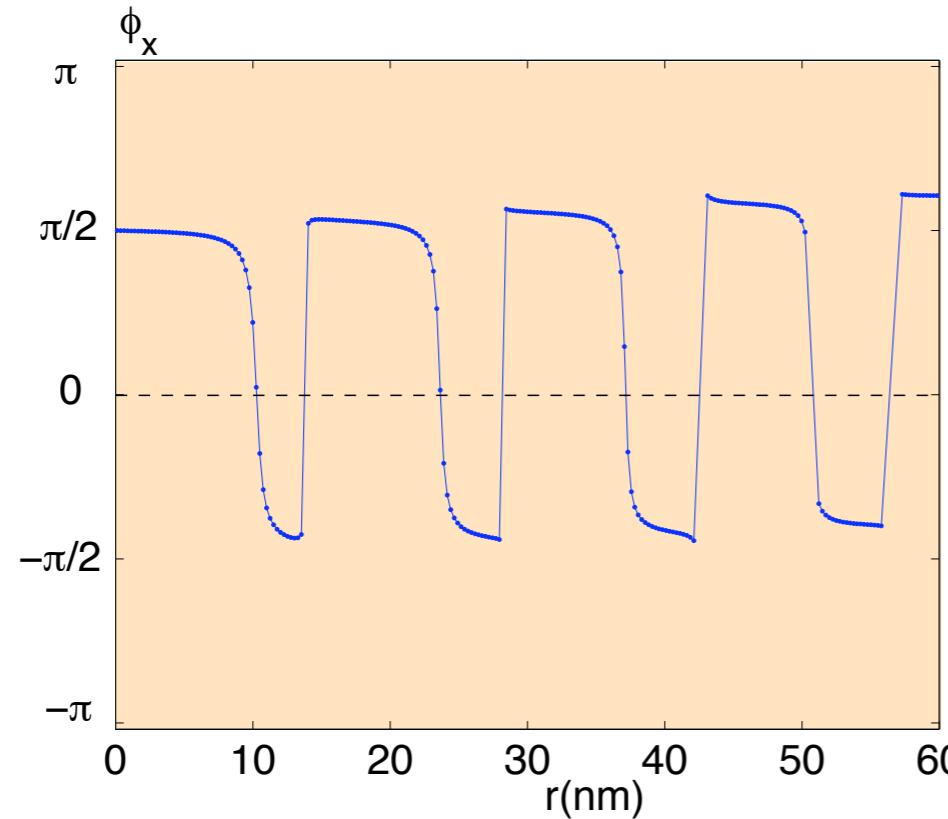

Weak Rashba regime with $\Delta_R/\epsilon_F < 1$

Modified RKKY oscillation with a gradual upwinding trend due to Rashba interaction.


Robust spiral backbone with minor oscillatory residues resembling the RKKY oscillations.

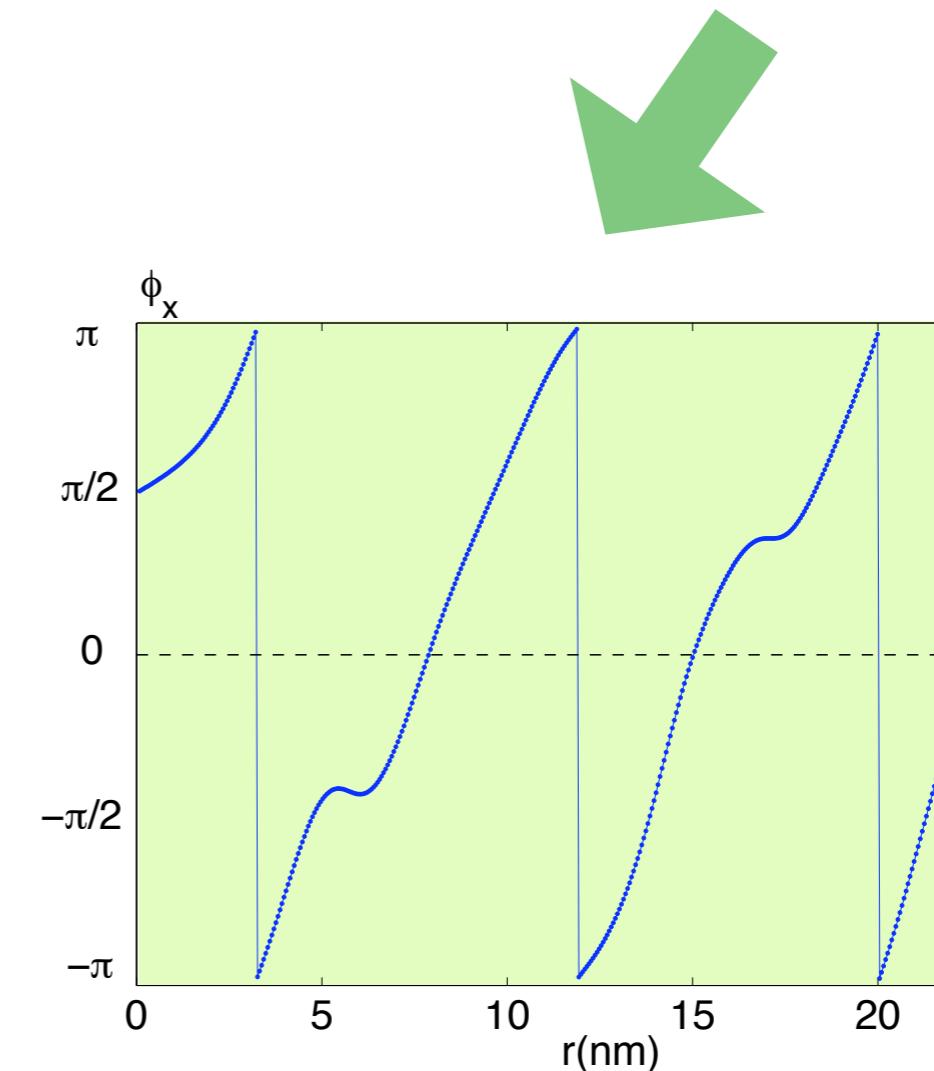




Dilute density regime with $\Delta_R/\epsilon_F > 1$

Fermi Surface Topology

By changing the carrier density, we can change the topology of the Fermi surfaces from **two disks** (with opposite chiralities) to **one ring** (with one chirality).



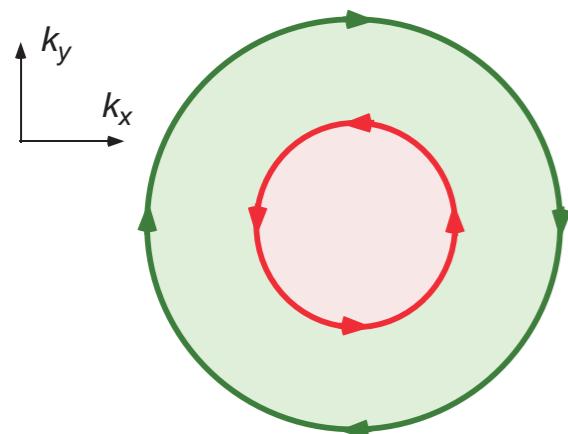


Lifshitz Transition

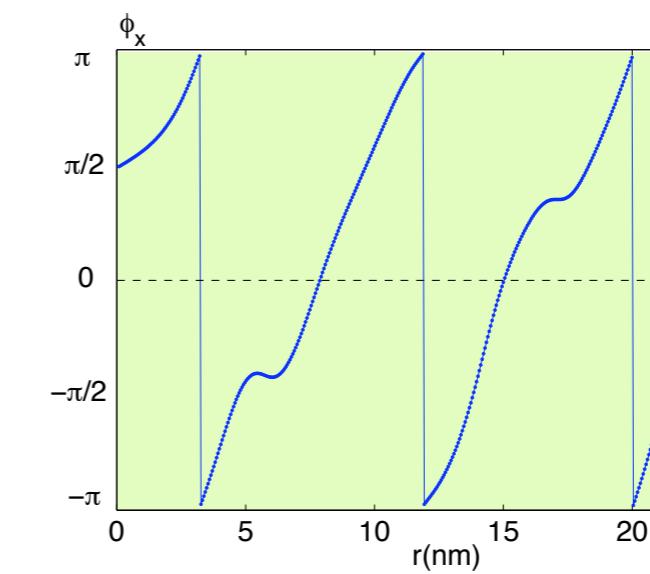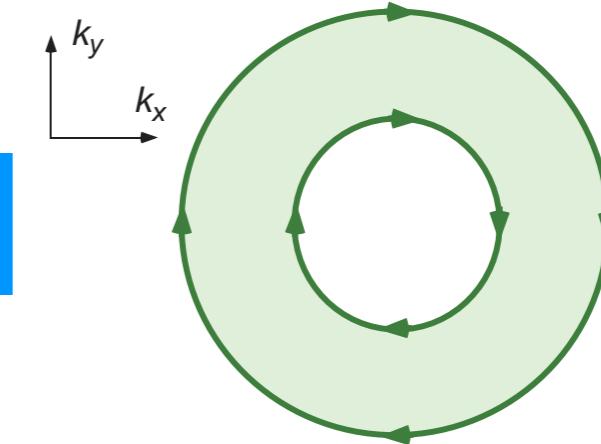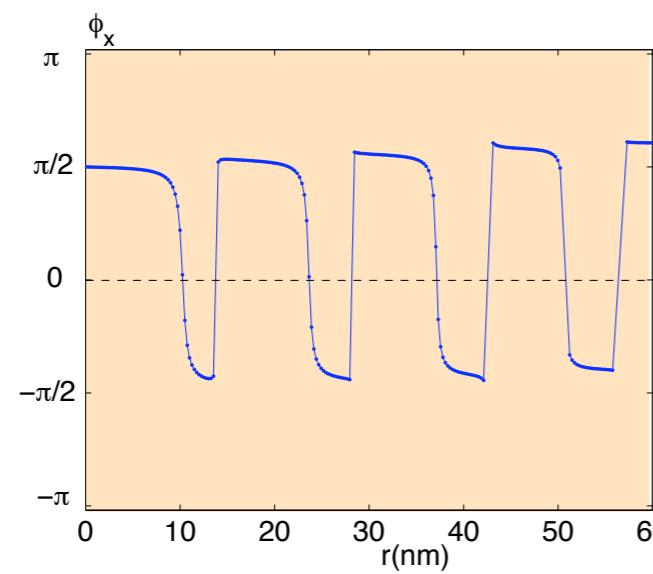



SUMMARY I

- ◆ Carrier-mediated ferromagnetism in diluted magnetic semiconductor.
- ◆ Self-consistent Green's function approach for spin-wave dynamics.
- ◆ Strong correlation between magnetization curve and spin relaxation rate.
- ◆ More needs to be done ...

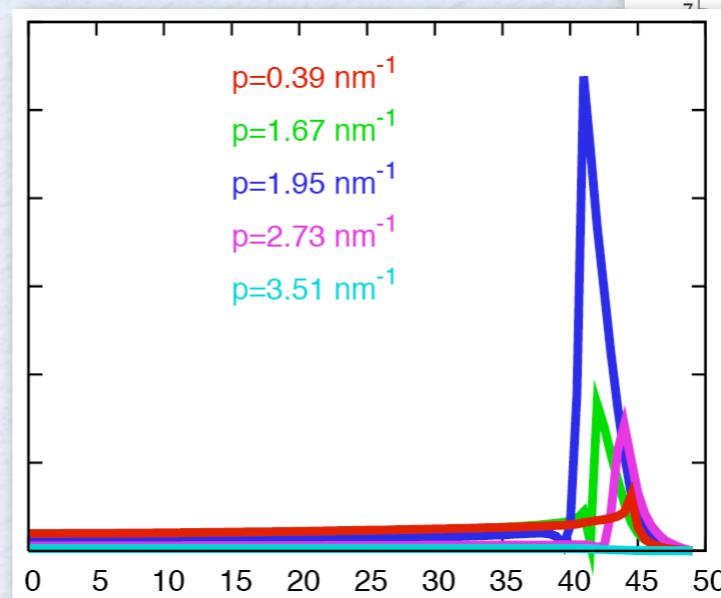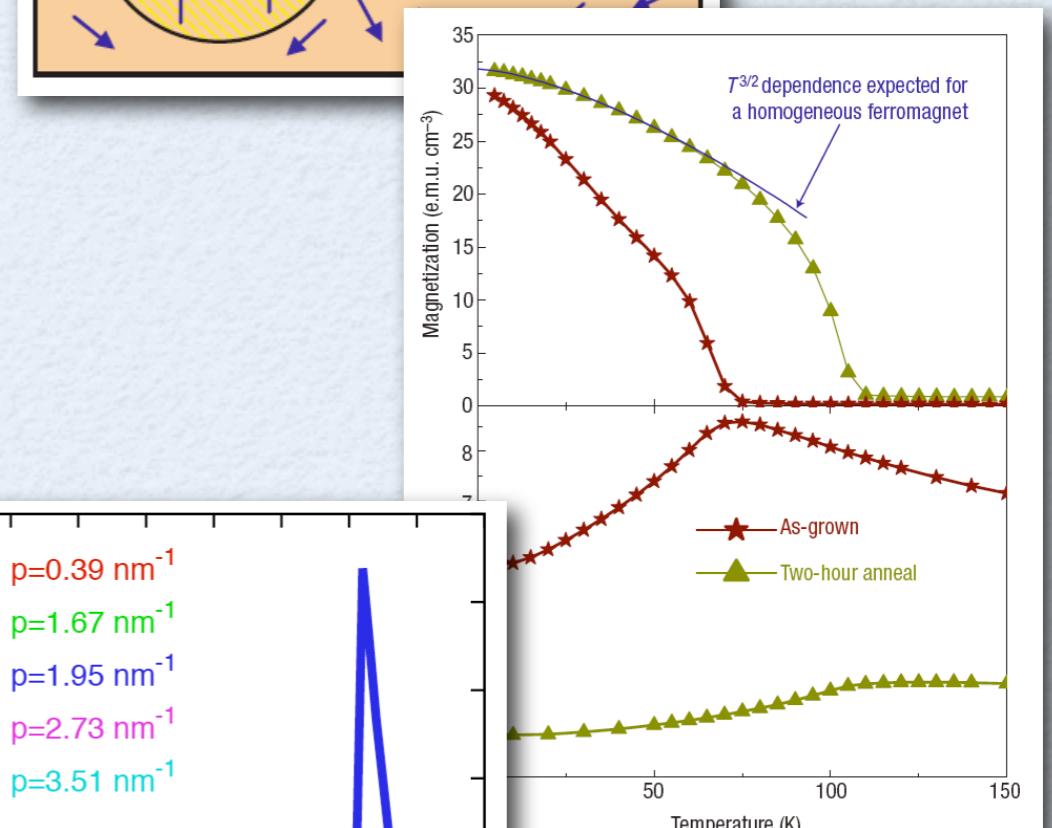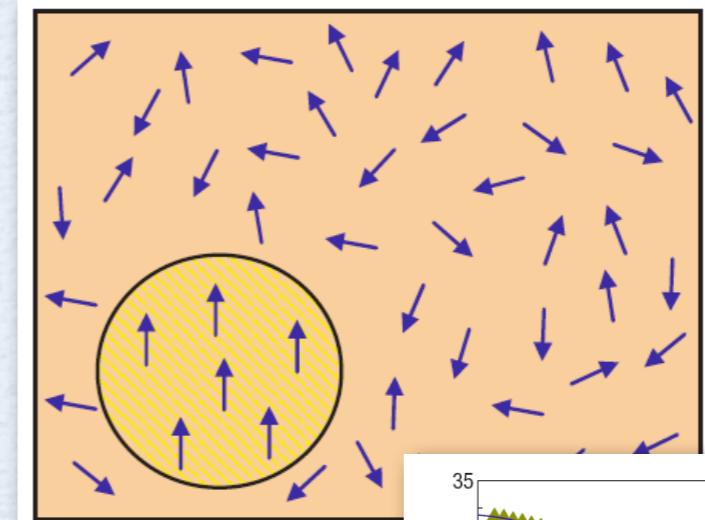

SUMMARY II

- ◆ Non-collinear exchange coupling mediated by Rashba interaction.
- ◆ RKKY or Spiral? Depending on the Fermi surface topology.
- ◆ Liftshitz transition by changing the carrier density in the 2DEG.
- ◆ Potential applications? Ballistic vs diffusive? & Lots of open questions...

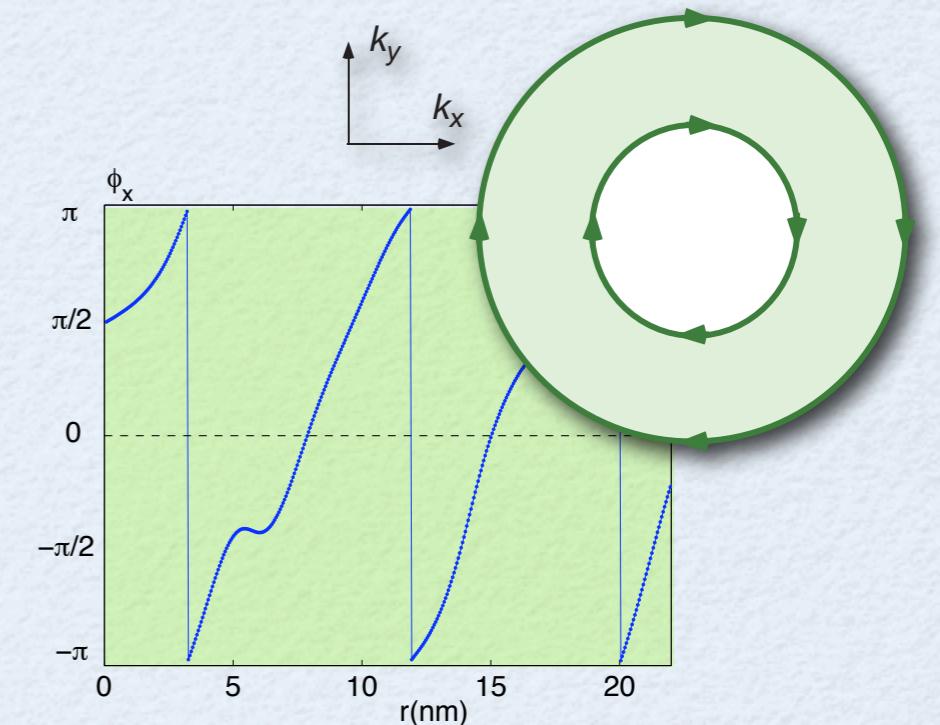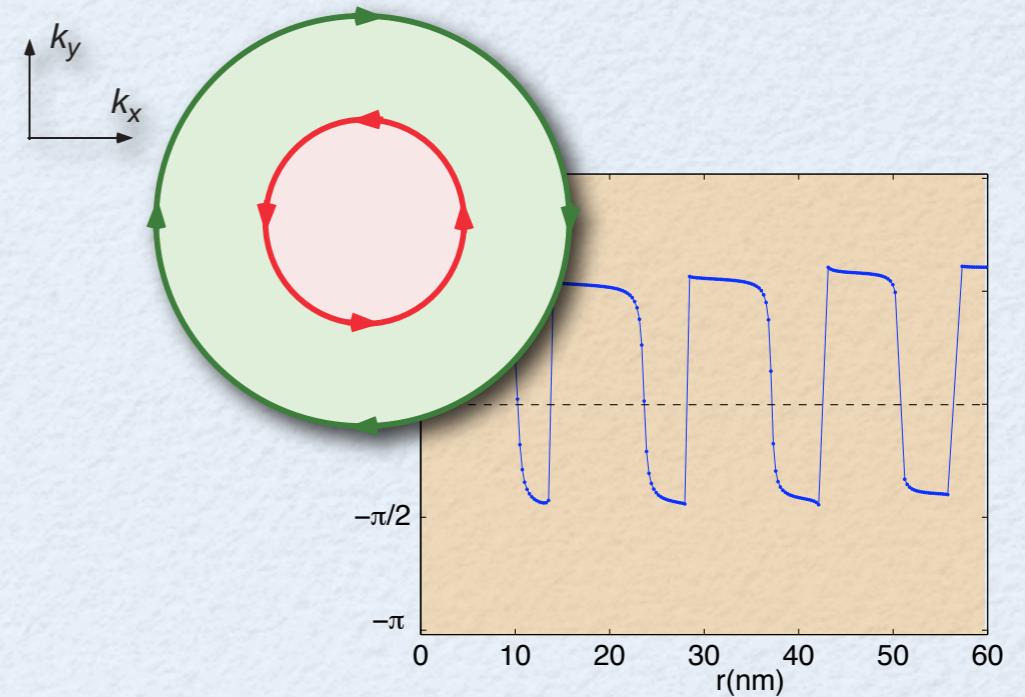



THANK YOU!!